

Novel push-pull thieno[2,3-*b*]indole-based dyes for efficient dye-sensitized solar cells (DSSCs)

Roman A. Irgashev,^{*a,b} Arseny A. Karmatsky,^{a,b} Grigory A. Kim,^a Alexey A. Sadovnikov,^c Viktor V. Emets,^d Vitaly A. Grinberg,^d Vladimir K. Ivanov,^{c,e} Sergey A. Kozyukhin,^{c,e} Gennady L. Rusinov,^{a,b} and Valery N. Charushin^{a,b}

^a Postovsky Institute of Organic Synthesis, Ural Division of the Russian Academy of Sciences, Ekaterinburg, 620990, Russia

^b Ural Federal University named after the First President of Russia, B. N. Yeltsin, Ekaterinburg, 620002, Russia

^c Kurnakov Institute of General and Inorganic Chemistry RAS, Moscow, 11999, Russia

^d Frumkin Institute of Physical Chemistry and Electrochemistry RAS, Moscow, 119071, Russia

^e Department of Chemistry, National Research Tomsk State University, Tomsk, 634050, Russia

E-mail: irgashev@ios.uran.ru


Received 09-21-2017

Accepted 01-22-2017

Published on line 04-21-2017

Abstract

New metal-free sensitizers (**IK 3-6**), based on the thieno[2,3-*b*]indole ring system, bearing various aliphatic substituents at the nitrogen atom (electron-donating part), several thiophene units (π -bridge linker) and 2-cyanoacrylic acid (the electron-accepting and anchoring group) have been synthesized for application in dye-sensitized solar cells (DSSCs). The relationship between the IK dye structure and efficiency of the corresponding DSSC has been elucidated. Power conversion efficiency (PCE) up to 6.3% (short-circuit photocurrent density (J_{sc}) 19.0 mA cm⁻², open-circuit voltage (V_{oc}) 0.59 V, and fill factor (FF) 56.4%) were obtained for the DSSC, based on 2-cyano-3-{5-[8-(2-ethylhexyl)-8*H*-thieno[2,3-*b*]indol-2-yl]thiophen-2-yl}acrylic acid (**IK 3**), which proved to be a highly synthetic available compound, under simulated AM 1.5 G irradiation (100 mW cm⁻²), thus indicating that thieno[2,3-*b*]indole-based organic dyes are perspective candidates for DSSCs.

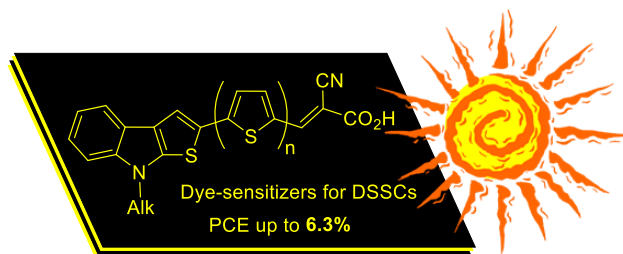


Keywords: Thieno[2,3-*b*]indole, electron-rich heterocycles, push-pull structure, metal-free dyes, photovoltaic properties, dye-sensitized solar cells

Results and Discussion

Synthesis of the IK dyes


A new dye-sensitizer **IK 3**, bearing a 2-ethylhexyl substituent at N-1 of the thieno[2,3-*b*]indole ring system, was obtained according to the same procedure, used for the synthesis of dyes **IK 1** and **IK 2**, described in the recently published paper.¹⁷ Namely, 2-(thien-2-yl)-substituted thieno[2,3-*b*]indole **1a** was formylated by using the Vilsmeier–Haack reaction to form the corresponding aldehyde **2a**. This aldehyde was condensed with 2-cyanoacetic acid to give the target dye **IK 3**, bearing a branched aliphatic chain at the nitrogen atom and only one thiophene unit, as a π -bridge linker for this push-pull system (Scheme 1).

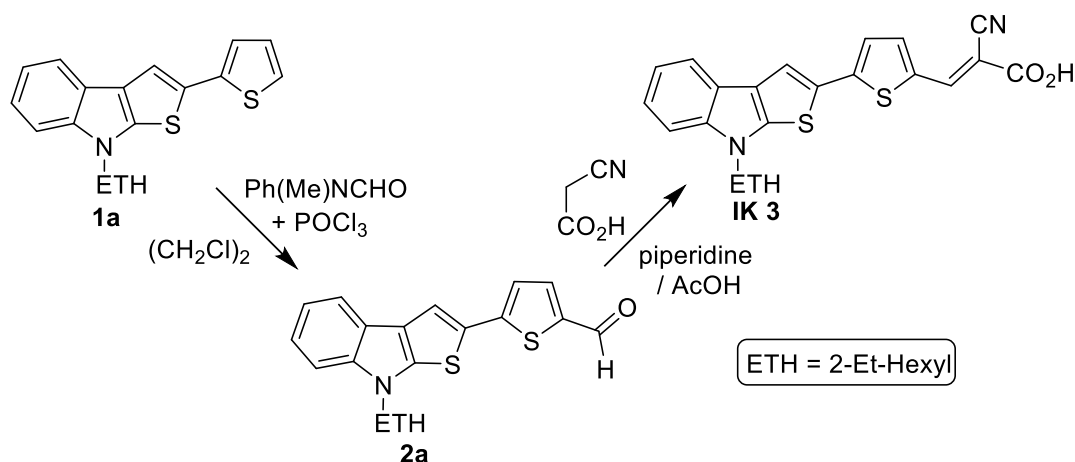

Scheme 1. The synthesis of thieno[2,3-*b*]indole dye **IK 3**.


A similar synthetic strategy was used to obtain thieno[2,3-*b*]indole dyes with a larger number of thiophene units in the π -bridge linker. Potential dye precursors **1c** and **1d** with 2,2'-bithiophene and 2,2':5',2''-terthiophene moieties were prepared according to the recently reported protocol for the synthesis of 2-(het)aryl-substituted thieno[2,3-*b*]indoles.²⁰ Interestingly, the cyclization of indolin-2-one **3b** with the Lawesson's reagent (LR) in refluxing toluene led to the formation of the protodebrominated thieno[2,3-*b*]indole **1b**, instead of the expected product **2-Br-1b**, which can be regarded as the starting material for the synthesis of compounds **1c,d**. We believe that the reductive cyclization of the intermediate **3b** by action of the Lawesson's reagent was accompanied by reductive debromination, which takes place, for instance, on treatment of 2-bromothiophenes with zinc powder in glacial acetic acid.²¹ Moreover, attempts to synthesize compound **2-Br-1b** through direct bromination of thieno[2,3-*b*]indole **1b** failed. To solve this problem, pre-functionalization of the 5-bromothiophen-2-yl part of indolin-2-one **3b** through the Stille cross-coupling reaction with 2-(tributylstannyl)thiophene was performed successfully, thus affording 2,2'-bithiophene-containing intermediate **3c** in 86% yield.

The target thieno[2,3-*b*]indole **1c** was obtained from compound **3c** using the typical cyclization procedure with the Lawesson's reagent. The terthiophene precursor **1d** was prepared through a similar cyclization of the corresponding indolin-2-one **3d**, obtained by condensation of *N*-(*n*-butyl)isatin with 5-acetylterthiophene (Scheme 2). The latter compound was synthesized by acetylation of 2,2':5',2''-terthiophene according to a slightly modified literature procedure.²²

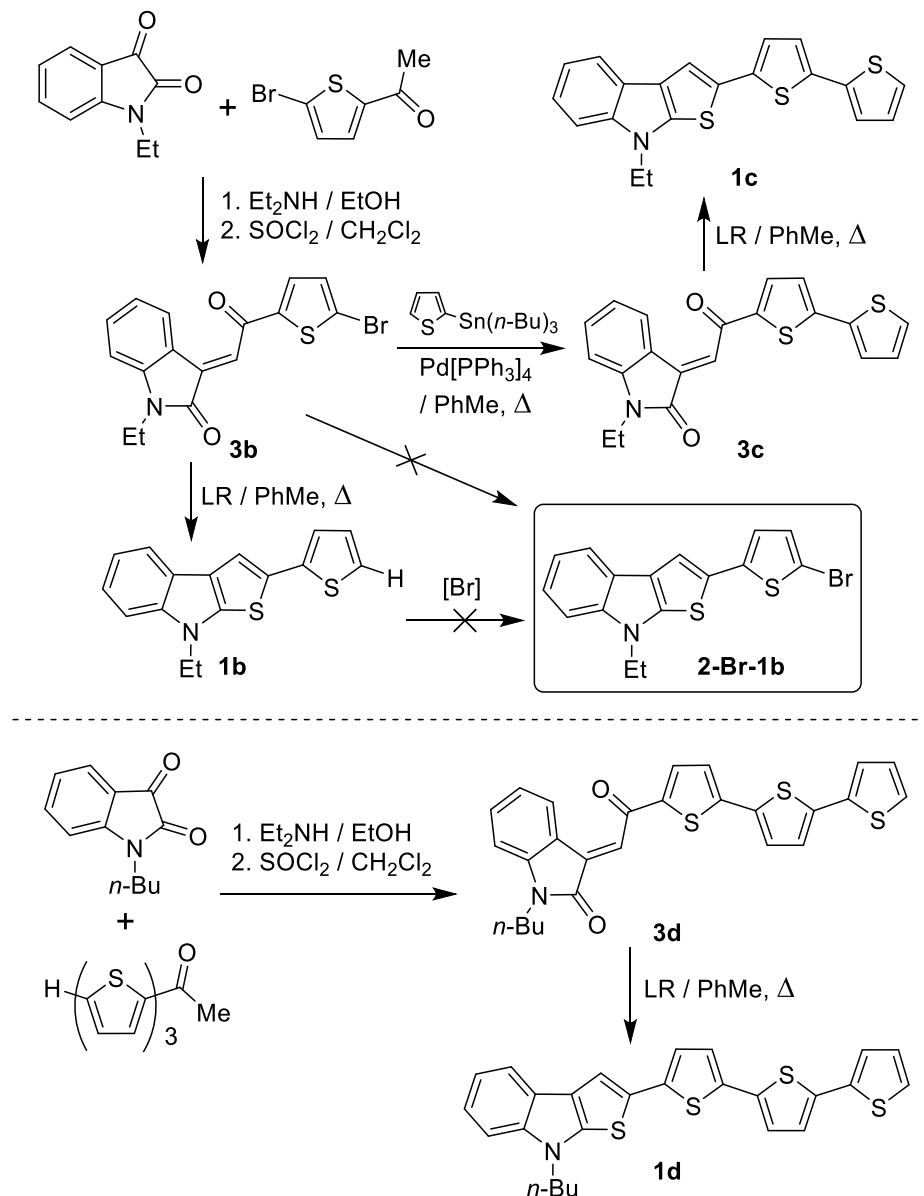

Scheme 2. Synthesis of thieno[2,3-*b*]indoles **1c** and **1d** with bi- and tertthiophene moieties.

The Vilsmeier-Haack formylation of compounds **1c** and **1d** was supposed to be the next step in the synthesis of the target dyes. Unfortunately, attempts to formylate the thieno[2,3-*b*]indoles in this way failed as rapid degradation of the starting materials **1c** and **1d** occurred on treatment with the Vilsmeier complex. As such, an alternative synthetic strategy was elaborated to produce thieno[2,3-*b*]indole dyes with an expanded π -conjugated system. The approach exploited included the conversion of thieno[2,3-*b*]indoles **1b** and **1e** into the corresponding stannanes **1B** and **1E**, followed by the Stille cross-coupling reaction of intermediate **1B** with 5-bromothiophene-2-carbaldehyde or intermediate **1E** with 5'-bromo-[2,2'-bithiophene]-5-carbaldehyde to produce thienaldehydes **2b** and **2d**, respectively. In a similar manner, thieno[2,3-*b*]indole **1c**, bearing 2,2'-bithiophene moiety, was transformed into aldehyde **2c**. Finally, new thieno[2,3-*b*]indole dyes **IK 4-6** were synthesized through the Knoevenagel condensation of functional thienaldehydes **2b-d** with 2-cyanoacetic acid in glacial acetic acid under reflux with piperidine, as the catalyst (Scheme 3).

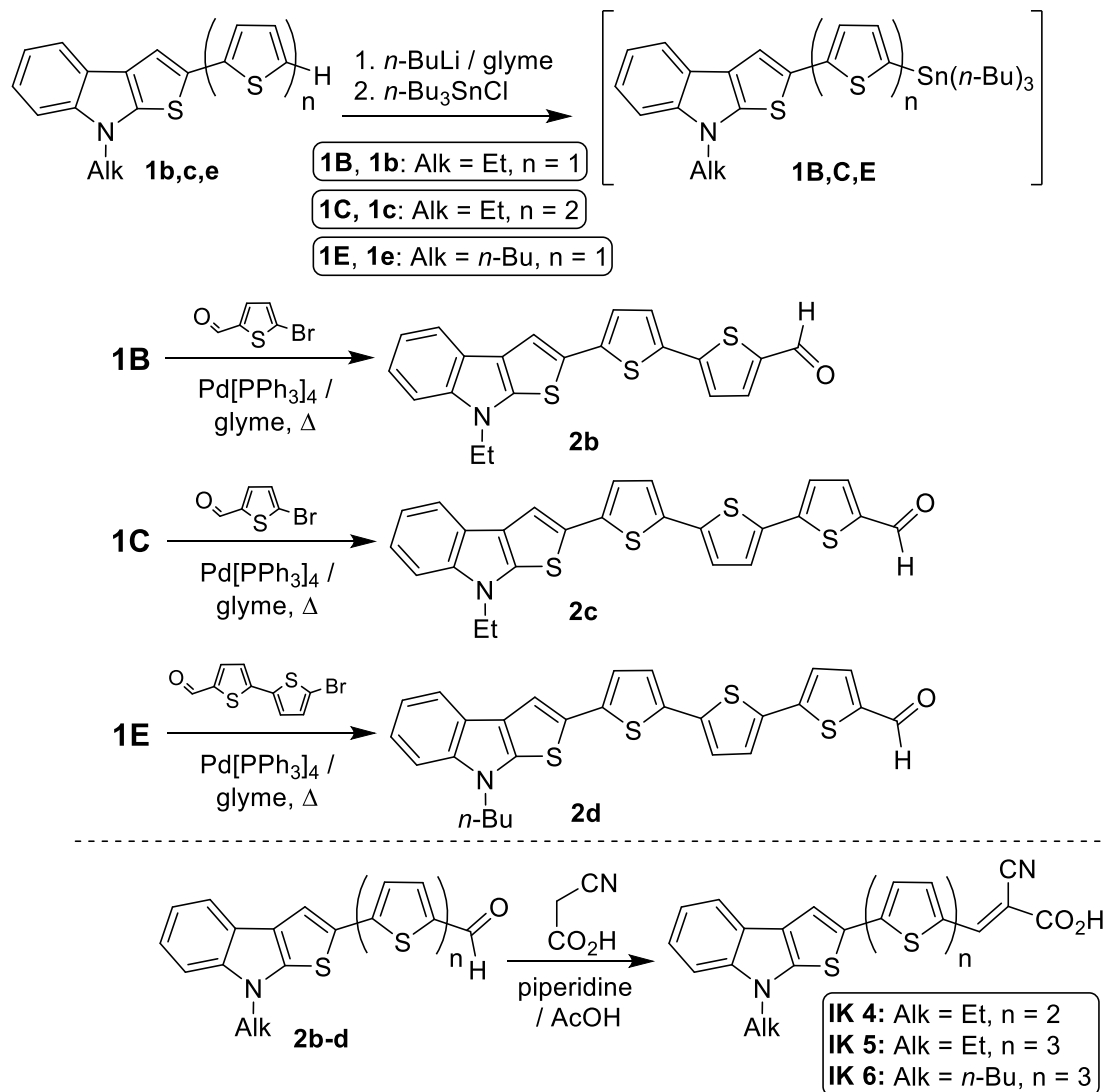

Scheme 3. Synthesis of 2-thienaldehydes **2b-d** and the corresponding dyes **IK 4-6**.

Optical and electrochemical measurements

UV-vis absorption spectra of the dyes **IK 3-6** in THF are shown in the Figure 2, and the spectral data are summarized in the Table 1. The 350-400 nm bands can be attributed to the localized $\pi \rightarrow \pi^*$ electron transition. The main absorption bands in the visible region of ~ 400 -600 nm with a high molar absorption are likely to originate from intramolecular charge transfer (ICT) transitions from the thieno[2,3-*b*]indole donating part of the molecules to electron-withdrawing fragment of 2-cyanoacrylic acid. The bathochromic shift caused by an increase in the number of thiophene units in the π -bridge can be observed due to $\pi \rightarrow \pi^*$ electron transition, that changes from ~ 320 nm (**IK 3**) and 364 nm (**IK 4**) to 398 nm (**IK 5** and **IK 6**). Also, this increase makes some bathochromic shift to ICT, but it can be observed only between one (**IK 3**) and two (**IK 4**) thiophene moieties. It is noteworthy that all dyes show a high visible molar extinction coefficient (from 42141 to 48773 M⁻¹cm⁻¹), thus indicating their good light-harvesting capability. However, the value of molar extinction in the group of these dyes is enhanced slightly, when the number of thiophenes units in the π -bridge linker is increased from one to three.

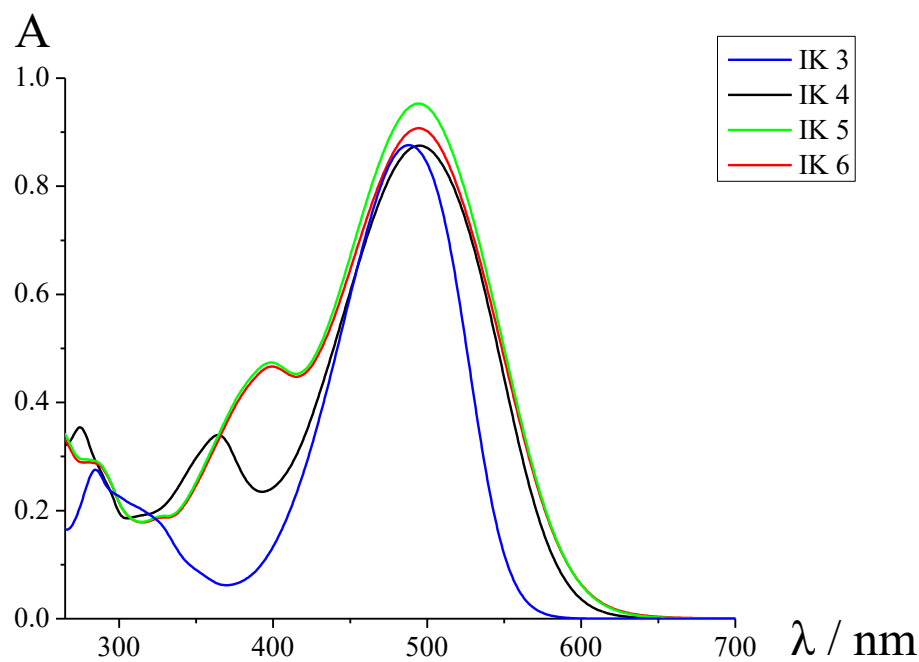


Figure 2. UV-vis absorption spectra of the IK dyes in $2 \cdot 10^{-5}$ M THF solution.

The diffuse reflectance spectra (DRS) of the **IK 3-6** solid compounds are shown in the Figure 3 as Kubelka-Munk function vs light energy. The Kubelka-Munk equation is expressed as follows:

$$F(R_d) = \frac{(1-R_d)^2}{2R_d},$$

R_d is the absolute reflectance of the sample layer. The optical band gap energies ($E_{\text{gap}}^{\text{opt}}$) were estimated from the extrapolation of the linear parts of corresponding curves to $F(R_d) = 0$. These data are summarized in the Table 1. The energy band gap can be easily tuned by increasing the number of thiophene units in the π -bridges, and the values of $E_{\text{gap}}^{\text{opt}}$ lie in the range from 1.51 to 1.82 eV. These values indicate the prospects of using the studied compounds as light-harvesting materials.

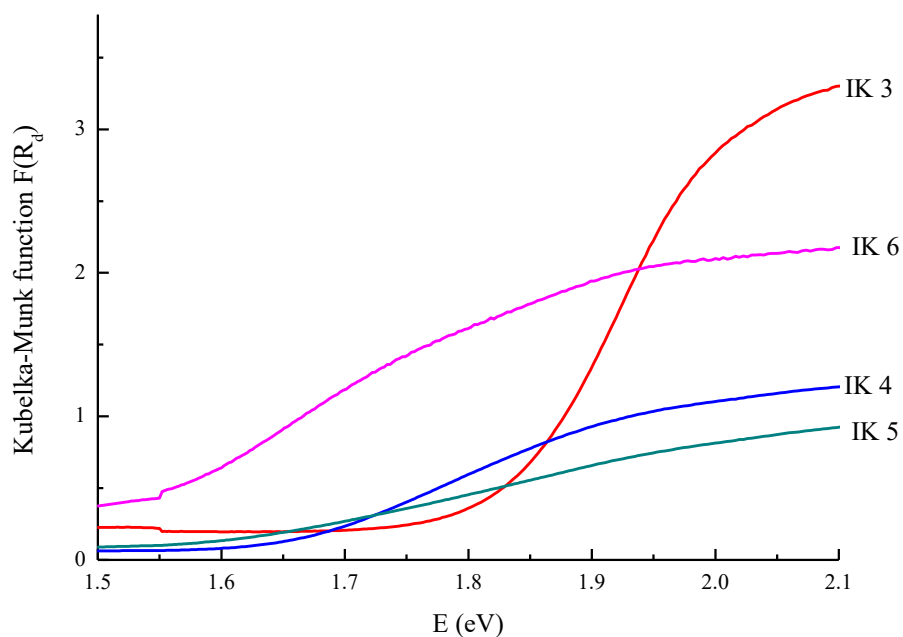
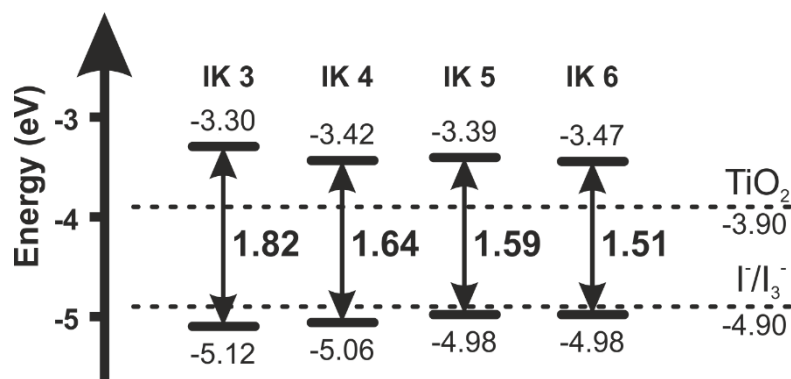


Figure 3. Reflectance spectra of solid samples **IK 3-6****Table 1.** Optical and electrochemical properties of the IK dyes

Dye	λ_{\max} (nm)	ϵ ($M^{-1}cm^{-1}$)	$E_{\text{gap}}^{\text{opt}}$ (eV) ^a	$E_{\text{Ox}}^{\text{onset}}$ (V) ^b	E_{HOMO} (eV) ^c	E_{LUMO} (eV) ^d
IK 3	488	42820	1.82	0.47	-5.12	-3.30
IK 4	495	42141	1.64	0.41	-5.06	-3.42
IK 5	494	48773	1.59	0.33	-4.98	-3.39
IK 6	494	44426	1.51	0.33	-4.98	-3.47

^a $E_{\text{gap}}^{\text{opt}}$ was estimated from the diffuse reflectance spectra of the IK dyes in solid state. ^b The Ag/AgNO₃ reference electrode was calibrated using ferrocene/ferrocenium redox couple (Fc/Fc⁺). ^c E_{HOMO} (eV) = - [$E_{\text{Ox}}^{\text{onset}}$ - $E_{1/2}(\text{Fc}/\text{Fc}^+) + 4.8$], where $E_{1/2}(\text{Fc}/\text{Fc}^+)$ is the half-wave potential of the Fc/Fc⁺ couple against the Ag/Ag⁺ electrode. It was defined at 0.15 V in the calibration experiment. ^d $E_{\text{LUMO}} = E_{\text{HOMO}} + E_{\text{gap}}^{\text{opt}}$.

Electrochemical characteristics of the dyes **IK 3-6** were measured by cyclic voltammetry (CV) in a THF/MeCN (v/v, 1:1) solution of 0.1 M LiClO₄, as the supporting electrolyte at a scan rate of 100 mV/s, and the results obtained are listed in the Table 1. Thus, the HOMO energy levels of sensitizers **IK 3-6**, that correspond to the first oxidation potential of each dye, were determined from the CV data.

**Figure 4.** HOMO and LUMO energy levels diagram of dyes **IK 3-6**.

The LUMO energy levels of these dyes were calculated from the optical energy band gaps, estimated from the diffuse reflectance spectra, and E_{HOMO} values. The HOMO energy levels of all four dyes are more positive, than the I⁻/I₃⁻ redox couple (-4.9 eV), making possible regeneration of oxidized dye molecules after injection of excited electrons into TiO₂ electrode. On the other hand, the latter process is energetically permitted for each of these dyes because of their LUMO energy levels are more negative than the conduction edge of the TiO₂ (-3.9 eV) (Figure 4).

Photovoltaic measurements

Photovoltaic properties of DSSCs. DSSCs were fabricated using the synthesized dyes **IK 3-6**, as photosensitizers, and their photovoltaic properties were measured under standard global AM 1.5 irradiation (100 mW cm²). In addition, DSSCs based on recently described sensitizers **IK 1** and **2**,¹⁷ that represent a structurally close series of thieno[2,3-*b*]indole dyes, were also tested under similar experimental conditions. It is important to note that only formal applicability of dyes **IK 1** and **2** as sensitizers for DSSCs has been shown in our previous work.¹⁷ In particular, PCE values of the obtained solar cells were very low (PCE = 0.37 % for **IK 1**;

PCE = 0.79% for **IK 2**). These low PCE values were attributed to a number of defects of TiO₂ photoanodes, which were manufactured and used in that study.¹⁷

In contrast, the manufacturing technique of TiO₂ electrodes has been significantly improved during current research, which allowed us to obtain photovoltaic devices based on the investigated dyes with better PCE characteristics. Furthermore, the photosensitize capabilities of all IK dyes have been compared with commercial ruthenium dye **N3** cell performance. The photocurrent – voltage curves are depicted in the Figure 5, and the detailed parameters of short-circuit current density (J_{sc}), open-circuit voltage (V_{oc}), fill factor (FF) as well as total power conversion efficiency (PCE) are summarized in the Table 2.

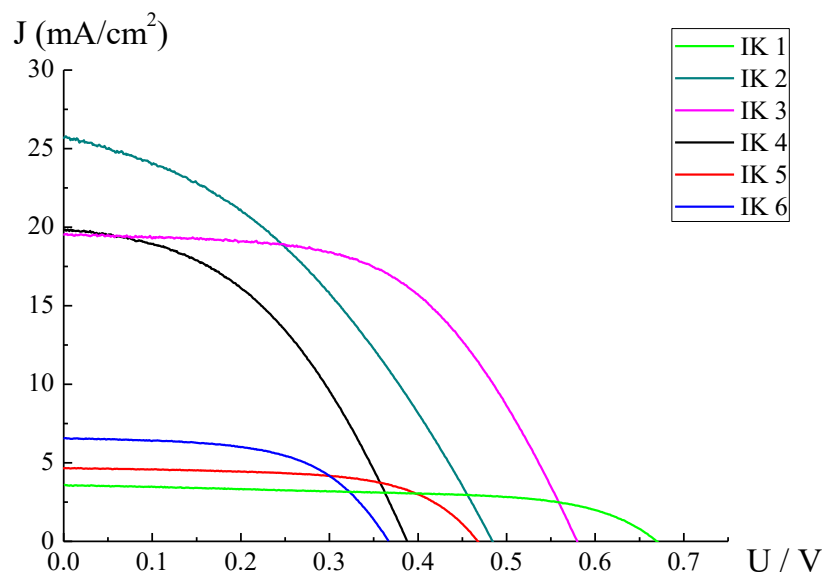


Figure 5. Photocurrent –voltage curves of the DSSCs based on the IK dyes.

Table 2. Photovoltaic performances of DSSCs based on the IK dyes and **N3**

Dye	J_{sc} (mA cm ⁻²)	V_{oc} (V)	FF (%)	PCE (%)
IK 1	3.6	0.67	59.5	1.4
IK 2	25.8	0.48	38.3	4.8
IK 3	19.0	0.59	56.4	6.3
IK 4	19.9	0.39	43.5	3.4
IK 5	4.7	0.47	60.5	1.3
IK 6	6.6	0.37	55.8	1.4
N3 ^{a,b}	<16.5±3.0>	<0.71±0.04>	<53.3±6.6>	<6.1±0.1>

^a **N3** - *cis*-diisothiocyanato-bis(2,2'-bipyridyl-4,4'-dicarboxylic acid) ruthenium(II). ^b For reference dye parallel measurements were performed on five identical photoanodes that allowed to calculate the error.

The formal relationship between the structure of the IK dyes and PCE of solar cells is visualized in the Figure 6. A significant increase of PCEs of cells based on dyes **IK 1-3**, having one thiophene unit ($n = 1$) in the π -bridge linker, was observed with increasing length of aliphatic chain (Alk = Et, Bu and ETH) at the nitrogen atom of their thieno[2,3-*b*]indole donating part. The DSSC based on dye **IK 3** showed the highest PCE of 6.3% with J_{sc} of 19.0 mA cm⁻², V_{oc} of 0.59 V and FF of 56.4%. Furthermore, the PCE value for DSSC with **IK 3** was comparable with that of the cell based on the commercially available ruthenium dye **N3**, one of the well-

known standard dyes. At the same time, the efficiency of cells based on **IK 1**, **IK 4**, and **IK 5** (Alk = Et; n = 1, 2 and 3, respectively) proved first to be increasing, and then decreasing sharply, while more thiophene units are involved gradually into the structure of π -bridge linker. However, replacement of the ethyl group at the nitrogen atom of thieno[2,3-*b*]indole donating part (compound **IK 5**, PCE = 1.3%) with the butyl substituent (**IK 6**, PCE = 1.4%) does not influence the PCE values of the cells.

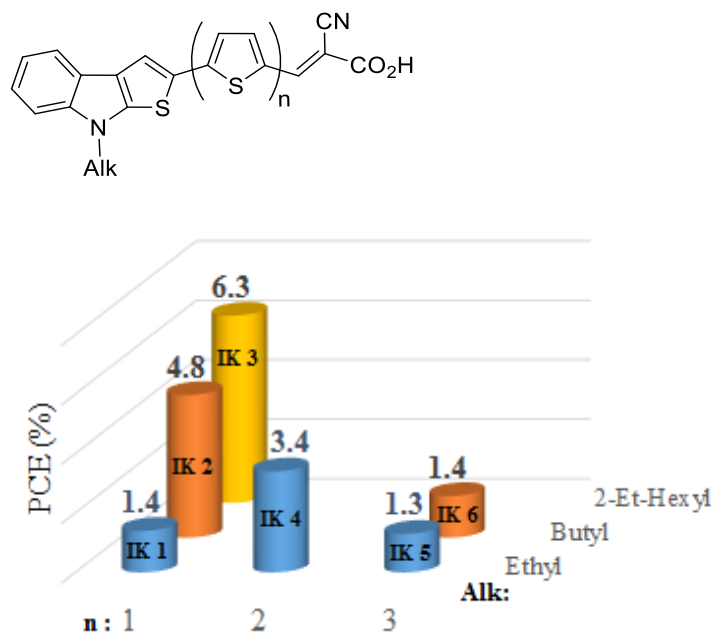


Figure 6. Relationship between the IK dye structure and PCE values of the related DSSCs.

Thus, DSSCs based on dyes **IK 1**, **IK 5** and **IK 6** were characterized by low PCE values linked with a poor photocurrent. The main reason for low J_{SC} values is proposed to be that dyes **IK 1**, **5** and **6**, having an insufficient size of aliphatic chain in their donating part and a high coplanar and π -conjugated structure, were capable of self-aggregation on the surface of TiO_2 photoanode, thus decreasing electron-injection yields. Indeed, it has previously been reported in the literature that unfavorable aggregation of dye molecules on TiO_2 film is the reason of excited-state quenching of the dyes, and as a consequence it leads to losses during the electron-injection process.²³⁻²⁶

Transients of photocurrent

Figure 7 shows the transient of the photocurrent for DSSC with a photoanode sensitized by the dye **IK 3**. One can see that the potential shifted rapidly into the negative direction in case of illuminating photoanode with **IK 3**, which indicated a high rate of accumulation of injected electrons in the conduction band of $nc-TiO_2$. The photocurrent density initially enhanced steeply under illumination with light output of 100mW cm^{-2} , and then the photocurrent stabilized. The transient of the photocurrent has a good rectangular form, as one can see in the Figure 7. This indicated that there were no diffusion limitations for dye **IK 3** regeneration and imposition of the dark electrochemical processes in case of the iodine–iodide mediator system. This result was confirmed by the absence of cathodic current at any potential of short circuit under dark conditions.

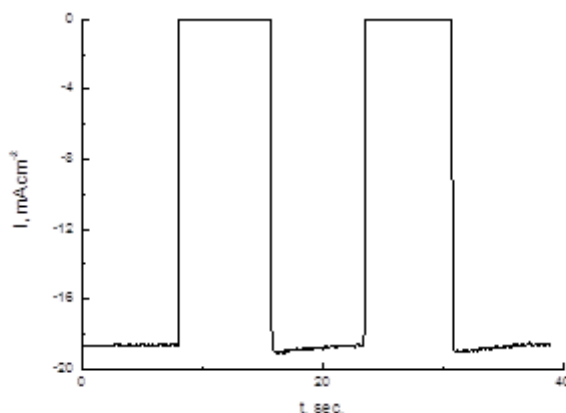


Figure 7. Time dependence of photocurrent for DSSC with photoanode with dye **IK 3** in the dark, and upon irradiation with light (100 mW/cm^2); scans recorded in acetonitrile solution in the presence of $0.5 \text{ M LiI} + 0.05 \text{ M I}_2$ at the potential of short circuit current density.

Conclusions

We have developed new organic dyes of the thieno[2,3-*b*]indole family, and used them successfully for sensitization of TiO_2 films in the DSSCs. The optical and redox properties of these dyes were investigated. All of these dyes show a strong light-harvesting ability in the visible region, and the LUMO and HOMO levels (estimated from their electrochemical and optical data) were suitably located for electron-injection and regeneration processes in the solar cell. An aliphatic substituent, in respect of its length and branching, located in the electron-donating part of sensitizers, decisively influenced solar cell efficiency, since it inhibits aggregation of the dye molecules onto TiO_2 surface by creating steric hindrances upon their adsorption. Indeed, the best result of solar energy-to-electricity conversion efficiency of 6.3% was achieved for the device based on the dye **IK 3**, having 2-Et-hexyl chain at the nitrogen atom of thieno[2,3-*b*]indole donor and only one thiophene unit in its π -bridge. In contrast, PCE values of the cells with dyes **IK 5** (1.3%) and **IK 6** (1.4%), containing 2,2':5',2''-terthiophene moiety, as the π -bridge linker, were significantly lower due to intermolecular π -stacking and aggregation processes in these dyes, proceeding on photoanode surface. It can be suggested that one of plausible ways to improve properties of these dyes is structural protection of oligothiophene π -bridge by long aliphatic chains, as it has previously been done for many metal-free dyes based on different electron-rich heterocycles or triaryl amines.^{4,27-29} On the other hand, dye-sensitizer **IK 3** is a synthetic available compound due to its preparation route is rather short and does not require any transition metal-catalysts or pyrophoric reagents, and this dye appears to be a very promising for DSSC application. In this regards, results reported herein indicate that the thieno[2,3-*b*]indole ring system is very perspective as electron-donating block for the further engineering of new sensitizers for high-performance DSSCs.

Experimental Section

General. ^1H and ^{13}C NMR spectra were obtained on Bruker DRX-400 and AVANCE-500 spectrometers, with TMS as the internal standard. The ^{13}C NMR spectrum of dye **IK 6** could not be determined due to a poor

solubility of this dye in a range of deuterated solvents. Elemental analyses were carried out on a Eurovector EA 3000 automated analyzer. Melting points were determined on a Boetius apparatus and were not corrected. IR spectra of samples (solid powders) were recorded on a Spectrum One Fourier transform IR spectrometer (Perkin Elmer), equipped with a diffuse reflectance attachment (DRA). UV-visible spectra were recorded for a $2 \cdot 10^{-5}$ M THF solution with Shimadzu UV-2401PC spectrophotometer. Cyclic voltammetry of the IK dyes was carried out for their $1 \cdot 10^{-3}$ M THF/MeCN (1:1) solutions with Metrohm Autolab PGSTAT128N potentiostat using a standard three-electrode cell, which was equipped with a platinum working electrode, a Ag/AgNO₃ (0.01 M) reference electrode, and a glassy carbon rod counter electrode. A three-electrode PECC-2 cell was used for photo-electrochemical measurements. The photoanode served as the working electrode and a platinum wire with the surface area of 5 cm² was used as the auxiliary electrode. In both electrochemical cells, a silver wire was used as the reference electrode. All potentials are given relative to this reference electrode. The voltammetric measurements were performed with an IPC Pro MF potentiostat under AM 1.5 global one sun of illumination (100 mW cm⁻²), provided by a solar simulator (Newport 96000). The illumination power at different distances was determined with a Nova apparatus (OPHIR-SPIRICON Inc.). The illuminated photoanode area was 0.125 cm². The illumination was performed from the side of a TiO₂ photoanode with the adsorbed dye. The time dependence of the photoanode and cathode potentials under the open-circuit conditions and the photocurrents at the short-circuit potential (transients) were measured under both illumination and in dark.

TiO₂ photoelectrode preparation. The preparation of photoelectrode was performed by adopting doctor-blade technique on a conducting glass TCO22-15 (2.9 × 2.9 cm² pieces) coated with a conductive fluorinated tin oxide (specific surface resistivity about 15 Ω/sq, Solaronix), which was purified by aging in a sulfochromic mixture, followed by ultra-sonication in organic solvents (isopropanol and acetone) and distilled water, and then dried at 50 °C in air. Application of Ti-nanoxide D/SP paste (Solaronix), comprising a nanocrystalline titanium dioxide, was performed by the adopting doctor-blade procedure, using a stencil with a square hole of 2.0 × 2.0 cm (~90 μm depth). After application of the paste, raw photoanodes were dried at 50 °C in air, and then calcined in a muffle furnace at 450 °C for 1 h (heating rate 3 °C/min, in air) The thickness of thus obtained titanium dioxide film was about 15 μm. Sensitizing of titanium dioxide was performed by soaking photoanodes in $5 \cdot 10^{-4}$ M THF solutions of dyes **IK 3-6** for 24 h.

DSSCs properties test. To measure photocurrent-voltage (J-V) characteristics, the DSSC was illuminated by light with energy of 100 mW·cm⁻² (AM 1.5) from a 150 W solar simulator (Newport, 96000). A computer-controlled IPC Pro MF potentiostat was employed to collect the J-V curves.

General procedure for the synthesis of indoline-2-ones (3b,d). The solution of 1-alkylisatin (3 mmol), corresponding acetylthiophene (3 mmol) and *N,N*-diethylamine (0.062 mL, 0.6 mmol) in EtOH (15 mL) was stirred at room temperature for 36 h. The resulting mixture was concentrated under reduced pressure and the residue was dissolved in dry CH₂Cl₂ (10 mL). SOCl₂ (0.28 mL, 3.9 mmol) was then added to the solution and the mixture was stirred at room temperature for 2 h. After that it was concentrated under reduced pressure and the residue was recrystallized from EtOH affording indolin-2-ones **3b,d** as dark-red needles.

3-[2-(5-Bromothiophen-2-yl)-2-oxoethylidene]-1-ethylindolin-2-one (3b). Red crystals; yield 750 mg (69%); mp 126–128 °C; ¹H NMR (400 MHz, DMSO-*d*₆) δ 8.34 (d, *J* 7.4 Hz, 1H), 8.01 (d, *J* 4.1 Hz, 1H), 7.66 (s, 1H), 7.50 – 7.43 (m, 2H), 7.13 (d, *J* 7.9 Hz, 1H), 7.06 (t, *J* 7.5 Hz, 1H), 3.77 (q, *J* 7.1 Hz, 2H), 1.18 (t, *J* 7.2 Hz, 3H); ¹³C NMR (126 MHz, DMSO-*d*₆) δ 181.50, 166.35, 146.80, 145.21, 136.67, 135.25, 133.42, 132.97, 127.63, 123.95, 123.78, 122.24, 119.40, 109.15, 34.29, 12.50; IR (DRA): 457, 492, 547, 573, 597, 645, 674, 688, 704, 748, 781,

790, 817, 855, 884, 905, 960, 990, 1015, 1028, 1060, 1075, 1107, 1132, 1152, 1236, 1287, 1317, 1352, 1384, 1409, 1466, 1521, 1598, 1619, 1646, 1712, 1767, 1805, 1922, 1957, 2935, 2987, 3094, 3125, 3402 cm^{-1} . Anal. Calcd. for $\text{C}_{16}\text{H}_{12}\text{BrNO}_2\text{S}$: C, 53.05; H, 3.34; N, 3.87. Found: C, 53.14; H, 3.36; N, 3.91%.

3-[2-([2,2':5',2''-Terthiophen]-5-yl)-2-oxoethylidene]-1-butylindolin-2-one (3d). Red crystals; yield 655 mg (46%); mp 158–160 °C; ^1H NMR (400 MHz, CDCl_3) δ 8.64 (d, J 7.7 Hz, 1H), 7.85 (d, J 4.1 Hz, 1H), 7.76 (s, 1H), 7.37 (td, J 7.6, 1.0 Hz, 1H), 7.31–7.27 (m, 2H), 7.25–7.21 (m, 2H), 7.14 (d, J 3.8 Hz, 1H), 7.08–7.02 (m, 2H), 6.82 (d, J 7.8 Hz, 1H), 3.76 (t, J 7.3 Hz, 2H), 1.74–1.64 (m, 2H), 1.48–1.36 (m, 2H), 0.97 (t, J 7.3 Hz, 3H); ^{13}C NMR (101 MHz, CDCl_3) δ 181.9, 168.0, 147.2, 145.7, 144.3, 139.2, 136.9, 136.5, 134.7, 134.2, 132.8, 128.9, 128.1, 126.9, 125.4, 124.7, 124.6, 124.5, 124.4, 122.7, 120.4, 108.4, 39.9, 29.5, 20.2, 13.7; IR (DRA): 459, 489, 535, 559, 574, 606, 625, 637, 649, 658, 690, 711, 750, 780, 796, 838, 883, 918, 939, 977, 1062, 1085, 1101, 1134, 1153, 1205, 1242, 1259, 1294, 1361, 1390, 1468, 1500, 1617, 1647, 1713, 1739, 1873, 1902, 2169, 2293, 2499, 2690, 2739, 2860, 2927, 2960, 3021, 3079, 3177, 3404 cm^{-1} . Anal. Calcd. for $\text{C}_{26}\text{H}_{21}\text{NO}_2\text{S}_3$: C, 65.65; H, 4.45; N, 2.94. Found: C, 65.61; H, 4.57; N, 3.06%.

Indolin-2-one 3c. A solution of compound **3b** (1.81 g, 5 mmol), 2-(tributylstannyl)thiophene (1.75 mL, 5.5 mmol) and $\text{Pd}(\text{Ph}_3\text{P})_4$ (0.29 g, 0.25 mmol) in toluene (30 mL) was stirred at 100 °C for 10 h under an argon atmosphere. Then the mixture was stirred with 10% aqueous solution of KF (70 mL) for 5 h. Toluene layer was separated, filtered through a silicagel pad and the solvent was removed under reduced pressure. The residue was recrystallized from EtOH/ CH_2Cl_2 giving red crystals of indolin-2-one **3c**.

3-[2-([2,2'-Bithiophen]-5-yl)-2-oxoethylidene]-1-ethylindolin-2-one (3c). Red crystals; yield 1.57 g (86%); mp 136–137 °C; ^1H NMR (400 MHz, $\text{DMSO}-d_6$) δ 8.39 (d, J 7.7 Hz, 1H), 8.12 (d, J 4.1 Hz, 1H), 7.73 (d, J 5.0 Hz, 1H), 7.71 (s, 1H), 7.64 (d, J 3.6 Hz, 1H), 7.50 (d, J 4.1 Hz, 1H), 7.48–7.44 (m, 1H), 7.21–7.18 (m, 1H), 7.13 (d, J 7.8 Hz, 1H), 7.09–7.04 (m, 1H), 3.78 (q, J 7.2 Hz, 2H), 1.19 (t, J 7.1 Hz, 3H); ^{13}C NMR (126 MHz, $\text{DMSO}-d_6$) δ 181.8, 166.5, 146.6, 145.1, 143.1, 136.0, 135.9, 135.2, 133.2, 128.9, 128.5, 127.6, 127.0, 125.5, 124.7, 122.2, 119.5, 109.1, 34.3, 12.5; IR (DRA): 456, 488, 548, 577, 594, 625, 646, 653, 696, 747, 760, 785, 801, 821, 845, 857, 901, 936, 971, 988, 1018, 1031, 1048, 1079, 1105, 1132, 1152, 1161, 1188, 1239, 1255, 1289, 1313, 1349, 1387, 1421, 1445, 1465, 1508, 1611, 1635, 1706, 1789, 1941, 2679, 2876, 2936, 2977, 3077, 3109, 3402 cm^{-1} . Anal. Calcd. for $\text{C}_{20}\text{H}_{15}\text{NO}_2\text{S}_2$: C, 65.73; H, 4.14; N, 3.83. Found: C, 65.54; H, 4.28; N, 3.64%.

General procedure for the synthesis of thieno[2,3-*b*]indoles (1c and 1d). The mixture of indolin-2-one **3c** or **3d** (2 mmol) and the Lawesson's reagent (0.81 g, 2 mmol) in dry toluene (10 mL) was refluxed for 1 h. Upon refluxing the color of the solution turns from dark-red to yellow. The resulting solution was concentrated under reduced pressure and the residue was purified by column chromatography (silica gel, CH_2Cl_2 /hexane 1:2) to give yellow powders of thieno[2,3-*b*]indoles **1c** and **1d**, respectively.

2-([2,2'-Bithiophen]-5-yl)-8-ethyl-8H-thieno[2,3-*b*]indole (1c). Yellow powder; yield 430 mg (59%); mp 130–131 °C; ^1H NMR (500 MHz, $\text{DMSO}-d_6$) δ 7.84 (d, J 7.8 Hz, 1H), 7.74 (s, 1H), 7.61 (d, J 8.3 Hz, 1H), 7.53 (dd, J 5.1, 1.1 Hz, 1H), 7.33 (dd, J 3.6, 1.1 Hz, 1H), 7.30–7.25 (m, 2H), 7.21 (d, J 3.8 Hz, 1H), 7.17 (td, J 7.6, 0.9 Hz, 1H), 7.11 (dd, J 5.1, 3.6 Hz, 1H), 4.35 (q, J 7.2 Hz, 2H), 1.41 (t, J 7.2 Hz, 3H); ^{13}C NMR (126 MHz, $\text{DMSO}-d_6$) δ 141.3, 140.9, 136.9, 136.1, 134.0, 128.4, 127.4, 125.4, 124.8, 123.9, 123.1, 122.2, 121.3, 119.6, 119.3, 115.4, 110.0, 40.4, 13.6; IR (DRA): 470, 667, 700, 744, 777, 796, 813, 838, 845, 881, 896, 926, 943, 963, 1014, 1052, 1081, 1129, 1159, 1188, 1206, 1230, 1252, 1276, 1330, 1349, 1401, 1424, 1438, 1453, 1466, 1480, 1505, 1522, 1555, 1570, 1592, 1632, 1671, 1688, 1743, 1767, 1797, 1885, 1924, 2874, 2935, 2981, 3059, 3100 cm^{-1} . Anal. Calcd. for $\text{C}_{20}\text{H}_{15}\text{NS}_3$: C, 65.72; H, 4.14; N, 3.83. Found: C, 65.71; H, 4.10; N, 3.65%.

2-([2,2':5',2''-Terthiophen]-5-yl)-8-butyl-8H-thieno[2,3-b]indole (1d). Yellow needles; yield 340 mg (36%); mp 145–147 °C; ¹H NMR (500 MHz, CDCl₃) δ 7.78 (d, *J* 7.7 Hz, 1H), 7.46 (s, 1H), 7.36 (d, *J* 8.2 Hz, 1H), 7.30–7.26 (m, 1H), 7.21 (dd, *J* 5.1, 1.1 Hz, 1H), 7.20–7.16 (m, 2H), 7.08 (d, *J* 3.8 Hz, 1H), 7.06 (dd, *J* 3.7, 2.8 Hz, 2H), 7.03–7.00 (m, 2H), 4.19 (t, *J* 7.1 Hz, 2H), 1.96–1.87 (m, 2H), 1.44–1.35 (m, 2H), 0.96 (t, *J* 7.4 Hz, 3H); ¹³C NMR (126 MHz, CDCl₃) δ 142.9, 141.6, 138.1, 137.2, 136.2, 136.0, 134.6, 128.3, 127.9, 124.5, 124.4, 124.2, 123.9, 123.7, 123.5, 122.8, 122.1, 122.1, 119.6, 119.6, 119.4, 115.0, 109.4, 46.1, 30.9, 20.3, 13.7; IR (DRA): 463, 497, 554, 582, 607, 684, 735, 750, 789, 811, 823, 838, 862, 911, 925, 1016, 1036, 1068, 1120, 1116, 1132, 1209, 1222, 1236, 1252, 1267, 1288, 1332, 1364, 1380, 1410, 1424, 1435, 1456, 1480, 1499, 1515, 1541, 1569, 1606, 1638, 1747, 1780, 1872, 1909, 2680, 2868, 2928, 2959, 3070 cm⁻¹. Anal. Calcd. for C₂₆H₂₁NS₄: C, 65.64; H, 4.45; N, 2.94. Found: C, 65.68; H, 4.37; N, 2.98%.

5-[8-(2-Ethylhexyl)-8H-thieno[2,3-b]indol-2-yl]thiophene-2-carbaldehyde (2a). POCl₃ (1.4 mL, 15 mmol) was added to a solution of *N*-methylformanilide (1.85 mL, 15 mmol) in dry dichloroethane (30 mL) and the solution was stirred at room temperature for 30 min. Thieno[2,3-*b*]indole **1a** (1.84 g, 5 mmol) was added to the Vilsmeier reagent and the resulting mixture was stirred at room temperature for 96 h. Then the mixture was vigorously stirred with 5% NaHCO₃ (60 mL) for 3 h. The organic layer was separated and the solvent was evaporated under a reduced pressure. The residue was purified by column chromatography (silica gel, CH₂Cl₂) and aldehyde **2a** was obtained as a yellow powder; yield 1.56 g (79%); mp 105–106 °C; ¹H NMR (500 MHz, DMSO-*d*₆) δ 9.85 (s, 1H), 8.05 (s, 1H), 7.97 (d, *J* 4.0 Hz, 1H), 7.87 (d, *J* 7.7 Hz, 1H), 7.60 (d, *J* 8.3 Hz, 1H), 7.46 (d, *J* 4.0 Hz, 1H), 7.34–7.28 (m, 1H), 7.23–7.17 (m, 1H), 4.20 (d, *J* 7.6 Hz, 2H), 2.12–1.95 (m, 1H), 1.41–1.13 (m, 8H), 0.87 (t, *J* 7.4 Hz, 3H), 0.80 (t, *J* 7.1 Hz, 3H); ¹³C NMR (126 MHz, CDCl₃) δ 182.0, 149.3, 144.9, 142.2, 139.8, 137.6, 127.0, 123.8, 122.6, 122.0, 121.8, 119.9, 119.6, 117.6, 109.6, 50.4, 39.0, 30.7, 28.5, 24.1, 22.9, 13.9, 10.6; IR (DRA): 414, 434, 480, 533, 569, 579, 592, 619, 664, 694, 716, 745, 767, 791, 808, 826, 854, 910, 940, 971, 1015, 1050, 1132, 1163, 1191, 1214, 1234, 1261, 1305, 1333, 1366, 1382, 1437, 1481, 1506, 1537, 1571, 1609, 1649, 1713, 1762, 1890, 1939, 2102, 2482, 2668, 2741, 2799, 2867, 2928, 3052, 3290 cm⁻¹. Anal. Calcd. for C₂₃H₂₅NOS₂: C, 69.83; H, 6.37; N, 3.54. Found: C, 69.90; H, 6.14; N, 3.72%.

General procedure for the synthesis of thieno[2,3-*b*]indole-based thienaldehydes (2b-d). 1.6 M Solution of *n*-butyllithium in hexane (2.5 mL, 4 mmol) was added to the solution of thieno[2,3-*b*]indole **1b**, **1c** or **1e** (2 mmol) in dry glyme (15 mL) at 0 °C under an argon atmosphere. It was stirred at 0 °C for 1 h and then tributyltin chloride (1.08 mL, 4 mmol) was added dropwise at -40 °C. The mixture was stirred at room temperature overnight. The appropriate bromo-containing 2-thienaldehyde (2.2 mmol) and Pd(Ph₃P)₄ (0.18 g, 0.16 mmol) were added to the reaction mixture that was then heated at 95 °C for 8 h. Then the mixture was stirred with 10% KF (100 mL) for 5 h and extracted with EtOAc (100 mL). Organic layer was separated and the solvent was removed under reduced pressure. The residue was purified by column chromatography (silica gel, CH₂Cl₂) affording red powders of aldehydes **2b-d**.

5'-(8-Ethyl-8H-thieno[2,3-*b*]indol-2-yl)-[2,2'-bithiophene]-5-carbaldehyde (2b). Red powder; yield 400 mg (51%); mp 124–126 °C; ¹H NMR (500 MHz, CDCl₃) δ 9.81 (s, 1H), 7.78 (d, *J* 7.7 Hz, 1H), 7.61 (d, *J* 3.9 Hz, 1H), 7.49 (s, 1H), 7.36 (d, *J* 8.2 Hz, 1H), 7.29 (t, *J* 7.6 Hz, 1H), 7.24–7.15 (m, 3H), 7.02 (d, *J* 3.8 Hz, 1H), 4.23 (q, *J* 7.3 Hz, 2H), 1.50 (t, *J* 7.3 Hz, 3H); ¹³C NMR (126 MHz, CDCl₃) δ 182.3, 147.1, 142.7, 141.2, 141.1, 141.0, 137.4, 132.9, 127.6, 126.9, 123.8, 123.6, 122.8, 122.3, 122.0, 119.8, 119.5, 115.8, 109.3, 40.9, 13.7; IR (DRA): 411, 423, 471, 500, 553, 574, 603, 671, 700, 733, 780, 814, 841, 879, 917, 1016, 1046, 1082, 1132, 1161, 1224, 1255, 1333, 1380, 1453, 1485, 1506, 1524, 1555, 1573, 1666, 1722, 1839, 1880, 2091, 2265, 2482, 2666, 2798, 2878, 2937, 2980, 3062, 3293 cm⁻¹. MS (+ESI): Calcd. for C₂₁H₁₆NOS₃ *m/z* 394.0389 (M+H), found *m/z* 394.0383 (M+H).

5''-(8-Ethyl-8*H*-thieno[2,3-*b*]indol-2-yl)-[2,2':5',2''-terthiophene]-5-carbaldehyde (2c). Red powder; yield 290 mg (30%); mp 180–181 °C; ¹H NMR (500 MHz, CDCl₃) δ 9.86 (s, 1H), 7.80 (d, *J* 7.8 Hz, 1H), 7.67 (d, *J* 3.9 Hz, 1H), 7.50 (s, 1H), 7.38 (d, *J* 8.1 Hz, 1H), 7.32–7.28 (m, 2H), 7.24 (d, *J* 3.9 Hz, 1H), 7.20 (t, *J* 7.5 Hz, 1H), 7.14 (d, *J* 3.8 Hz, 1H), 7.12 (d, *J* 3.8 Hz, 1H), 7.05 (d, *J* 3.7 Hz, 1H), 4.28 (q, *J* 7.3 Hz, 2H), 1.53 (t, *J* 7.1 Hz, 3H); ¹³C NMR (126 MHz, CDCl₃) δ 182.3, 146.9, 142.5, 141.6, 141.2, 139.18, 139.15, 137.3, 134.2, 133.7, 128.0, 127.0, 125.1, 124.2, 124.0, 123.8, 122.8, 122.3, 122.2, 119.8, 119.5, 115.4, 109.3, 41.0, 13.8; IR (DRA): 417, 470, 512, 550, 575, 636, 670, 740, 790, 810, 858, 892, 906, 924, 945, 1015, 1049, 1135, 1161, 1222, 1250, 1282, 1331, 1381, 1402, 1459, 1502, 1538, 1572, 1609, 1672, 1883, 2113, 2351, 2496, 2728, 2809, 2929, 2965, 3059, 3309 cm⁻¹. Anal. Calcd. for C₂₅H₁₇NOS₄: C, 63.13; H, 3.60; N, 2.94. Found: C, 63.18; H, 3.51; N, 2.68%.

5''-(8-Butyl-8*H*-thieno[2,3-*b*]indol-2-yl)-[2,2':5',2''-terthiophene]-5-carbaldehyde (2d). Red powder; yield 230 mg (23%); mp 164–166 °C; ¹H NMR (500 MHz, CDCl₃) δ 9.86 (s, 1H), 7.79 (d, *J* 7.7 Hz, 1H), 7.67 (d, *J* 3.9 Hz, 1H), 7.50 (s, 1H), 7.38 (d, *J* 8.2 Hz, 1H), 7.33–7.27 (m, 2H), 7.24 (d, *J* 3.9 Hz, 1H), 7.22–7.18 (m, 1H), 7.14 (d, *J* 3.8 Hz, 1H), 7.12 (d, *J* 3.8 Hz, 1H), 7.05 (d, *J* 3.8 Hz, 1H), 4.22 (t, *J* 7.1 Hz, 2H), 1.99–1.87 (m, 2H), 1.49–1.36 (m, 2H), 0.97 (t, *J* 7.4 Hz, 3H); ¹³C NMR (126 MHz, CDCl₃) δ 182.3, 146.9, 143.0, 141.7, 141.6, 139.18, 139.15, 137.3, 134.2, 133.7, 128.0, 127.0, 125.1, 124.2, 123.9, 123.6, 122.8, 122.2, 122.0, 119.7, 119.5, 115.3, 109.4, 46.1, 30.9, 20.3, 13.7; IR (DRA): 435, 466, 511, 554, 586, 636, 667, 690, 715, 741, 782, 806, 845, 857, 895, 912, 927, 1016, 1047, 1066, 1117, 1136, 1161, 1226, 1251, 1267, 1282, 1332, 1362, 1378, 1406, 1456, 1479, 1504, 1571, 1609, 1659, 1742, 1890, 2110, 2497, 2725, 2796, 2872, 2932, 2958, 3061, 3295 cm⁻¹. Anal. Calcd. for C₂₇H₂₁NOS₄: C, 64.38; H, 4.20; N, 2.78. Found: C, 64.33; H, 4.12; N, 2.72%.

General procedure for the synthesis of thieno[2,3-*b*]indole-based dyes (IK 3-6). Piperidine (20 mg, 0.24 mmol) was added to a solution of aldehyde **2a-d** (1 mmol), 2-cyanoacetic acid (0.17 g, 2 mmol) in glacial AcOH (15 mL), and the resulting mixture was refluxed with stirring for 8 h. After cooling, the precipitate was filtered and washed with EtOH, affording desired dye **IK 3-6** as a black powder.

2-Cyano-3-{5-[8-(2-ethylhexyl)-8*H*-thieno[2,3-*b*]indol-2-yl]thiophen-2-yl}acrylic acid (IK 3). Black powder; yield 320 mg, (69%); mp 270–272 °C; ¹H NMR (500 MHz, DMSO-*d*₆) δ 13.63 (br. s, 1H), 8.46 (s, 1H), 8.10 (s, 1H), 7.96 (d, *J* 4.2 Hz, 1H), 7.91 (d, *J* 7.7 Hz, 1H), 7.60 (d, *J* 8.3 Hz, 1H), 7.51 (d, *J* 4.0 Hz, 1H), 7.34 – 7.29 (m, 1H), 7.22 – 7.18 (m, 1H), 4.21 (d, *J* 7.6 Hz, 2H), 2.10 – 2.01 (m, 1H), 1.41 – 1.12 (m, 8H), 0.87 (t, *J* 7.4 Hz, 3H), 0.80 (t, *J* 7.1 Hz, 3H); ¹³C NMR (126 MHz, DMSO-*d*₆) δ 163.9, 148.2, 146.2, 144.4, 142.2, 142.0, 132.2, 126.4, 123.9, 123.0, 122.9, 121.2, 120.0, 119.8, 118.9, 116.8, 110.4, 96.3, 49.6, 38.3, 29.9, 27.9, 23.5, 22.4, 13.8, 10.5; IR (DRA): 434, 460, 486, 529, 563, 580, 594, 626, 641, 667, 684, 737, 804, 842, 859, 898, 937, 1058, 1159, 1223, 1267, 1328, 1368, 1430, 1479, 1516, 1577, 1682, 1919, 2216, 2520, 2960 cm⁻¹. Anal. Calcd. for C₂₆H₂₆N₂O₂S₂: C, 67.50; H, 5.66; N, 6.06. Found: C, 67.43; H, 5.36; N, 6.06%.

2-Cyano-3-[5'-(8-ethyl-8*H*-thieno[2,3-*b*]indol-2-yl)-[2,2'-bithiophen]-5-yl]acrylic acid (IK 4). Black powder; yield 370 mg, (80%); mp 267–268 °C; ¹H NMR (400 MHz, DMSO-*d*₆) δ 13.68 (br. s, 1H), 8.47 (s, 1H), 7.97 (d, *J* 4.1 Hz, 1H), 7.89–7.81 (m, 2H), 7.61 (d, *J* 8.3 Hz, 1H), 7.59–7.54 (m, 2H), 7.31–7.27 (m, 2H), 7.18 (t, *J* 7.5 Hz, 1H), 4.35 (q, *J* 7.1 Hz, 2H), 1.41 (t, *J* 7.2 Hz, 3H); ¹³C NMR (126 MHz, DMSO-*d*₆) δ 163.6, 146.2, 145.5, 142.1, 141.6, 141.1, 140.3, 133.6, 132.0, 131.9, 130.9, 128.2, 126.9, 124.7, 123.7, 123.4, 122.5, 121.3, 119.8, 119.4, 116.6, 110.2, 40.5, 13.5; IR (DRA): 452, 479, 547, 582, 598, 627, 676, 697, 749, 784, 879, 944, 1053, 1093, 1221, 1330, 1442, 1481, 1511, 1572, 1687, 2217, 2933 cm⁻¹. Anal. Calcd. for C₂₄H₁₆N₂O₂S₃·0.3H₂O: C, 61.86; H, 3.59; N, 6.01. Found: C, 61.57; H, 3.41; N, 5.81%.

2-Cyano-3-[5''-(8-ethyl-8*H*-thieno[2,3-*b*]indol-2-yl)-[2,2':5',2''-terthiophen]-5-yl]acrylic acid (IK 5). Black powder; yield 375 mg, (69%); mp > 300 °C; ¹H NMR (500 MHz, DMSO-*d*₆) δ 13.69 (br. s, 1H), 8.45 (s, 1H), 7.94 (d, *J* 4.1 Hz, 1H), 7.83 (d, *J* 7.7 Hz, 1H), 7.74 (s, 1H), 7.59 (d, *J* 8.3 Hz, 1H), 7.58–7.53 (m, 2H), 7.36 (dd, *J* 7.3, 3.8

Hz, 2H), 7.28 (t, *J* 7.7 Hz, 1H), 7.21 (d, *J* 3.8 Hz, 1H), 7.17 (t, *J* 7.4 Hz, 1H), 4.33 (q, *J* 7.1 Hz, 2H), 1.40 (t, *J* 7.2 Hz, 3H); ¹³C NMR (126 MHz, DMSO-*d*₆) δ 163.6, 146.2, 145.2, 141.6, 141.4, 140.9, 138.2, 138.1, 133.9, 133.3, 132.7, 128.2, 127.2, 126.1, 125.2, 125.0, 123.4, 123.3, 122.3, 121.3, 119.6, 119.3, 116.5, 115.8, 110.1, 97.9, 40.4, 13.6; IR (DRA): 470, 516, 550, 581, 598, 625, 649, 693, 737, 774, 864, 932, 1050, 1217, 1446, 1482, 1506, 1584, 1682, 2218, 2981 cm⁻¹. Anal. Calcd. for C₂₈H₁₈N₂O₂S₄: C, 61.97; H, 3.34; N, 5.16. Found: C, 61.72; H, 3.37; N, 5.25%.

3-[5''-(8-Butyl-8H-thieno[2,3-*b*]indol-2-yl)-[2,2':5',2''-terthiophen]-5-yl]-2-cyanoacrylic acid (IK 6). Black powder; yield 410 mg, (72%); mp > 300 °C; ¹H NMR (400 MHz, DMSO-*d*₆) δ 13.75 (br. s, 1H), 8.48 (s, 1H), 7.98 (d, *J* 4.0 Hz, 1H), 7.84 (d, *J* 7.7 Hz, 1H), 7.78 (s, 1H), 7.64–7.58 (m, 3H), 7.42 (d, *J* 3.8 Hz, 1H), 7.40 (d, *J* 3.9 Hz, 1H), 7.32–7.24 (m, 2H), 7.17 (t, *J* 7.4 Hz, 1H), 4.32 (t, *J* 6.9 Hz, 2H), 1.89–1.79 (m, 2H), 1.37–1.25 (m, 2H), 0.90 (t, *J* 7.3 Hz, 3H); IR (DRA): 433, 474, 550, 583, 737, 782, 863, 935, 1016, 1048, 1214, 1431, 1479, 1508, 1571, 1684, 2220, 2491, 2957 cm⁻¹. Anal. Calcd. for C₃₀H₂₂N₂O₂S₄·0.3H₂O: C, 62.54; H, 3.95; N, 4.86. Found: C, 62.37; H, 3.80; N, 4.50%.

Acknowledgements

This research study was supported financially by the Russian Science Foundation (Project No. 16-13-10435).

Supplementary Material

¹H and ¹³C NMR spectra of new compounds and CV curves of dyes **IK 3-6**.

References

1. Green, M. A.; Emery, K.; Hishikawa, Y.; Warta, W.; Dunlop E. D. *Prog. Photovoltaics* **2015**, *23*, 1–9.
<http://dx.doi.org/10.1002/pip.2573>
2. O'Regan, B.; Grätzel, M. *Nature* **1991**, *353*, 737–740.
<http://dx.doi.org/10.1038/353737a0>
3. Yum, J.-H.; Jung, I.; Baik, C.; Ko, J.; Nazeeruddin, M. K.; Grätzel, M. *Energ. Environ Sci.* **2009**, *2*, 100–102.
<http://dx.doi.org/10.1039/B814863P>
4. Liang, M.; Chen, J. *Chem. Soc. Rev.* **2013**, *42*, 3453–3488.
<http://dx.doi.org/10.1039/c3cs35372a>
5. Liu, W. H.; Wu, I. C.; Lai, C. H.; Lai, C. H.; Chou, P. T.; Li, Y. T.; Chen, C. L.; Hsu, Y. Y.; Chi, Y. *Chem. Commun.* **2008**, 5152–5154.
<http://dx.doi.org/10.1039/B808535H>
6. Chen, B. S.; Chen, D. Y.; Chen, C. L.; Hsu, C. W.; Hsu, H. C.; Wu, K. L.; Liu, S. H.; Chou, P. T.; Chi, Y. *J. Mater. Chem.* **2011**, *21*, 1937–1945.
<http://dx.doi.org/10.1039/C0JM02433C>
7. Li, R. Z.; Lv, X. J.; Shi, D.; Zhou, D. F.; Cheng, Y. M.; Zhang, G. L.; Wang, P. *J. Phys. Chem. C* **2009**, *113*, 7469–7479.
<http://dx.doi.org/10.1021/jp900972v>

8. Zhang, G. L.; Bala, H.; Cheng, Y. M.; Shi, D.; Lv, X. J.; Yu, Q. J.; Wang, P. *Chem. Commun.* **2009**, 2198–2200.
<http://dx.doi.org/10.1039/B822325D>
9. Li, R. Z.; Liu, J. Y.; Cai, N.; Zhang, M.; Wang, P. *J. Phys. Chem. B* **2010**, *114*, 4461–4464.
<http://dx.doi.org/10.1021/jp101222s>
10. W. Zeng, Y. Cao, Y. Bai, Y. Wang, Y. Shi, M. Zhang, F. Wang, C. Pan, P. Wang, *Chem. Mater.* **2010**, *22*, 1915–1925.
<http://dx.doi.org/10.1021/cm9036988>
11. Horiuchi, T.; Miura, H.; Uchida, S. *Chem. Commun.* **2003**, 3036–3037.
<http://dx.doi.org/10.1039/B307819A>
12. Horiuchi, T.; Miura, H.; Sumioka, K.; Uchida, S. *J. Am. Chem. Soc.* **2004**, *126*, 12218–12219.
<http://dx.doi.org/10.1021/ja0488277>
13. Wang, Z.-S.; Koumura, N.; Cui, Y.; Takahashi, M.; Sekiguchi, H.; Mori, A.; Kubo, T.; Furube, A.; Hara, K. *Chem. Mater.* **2008**, *20*, 3993–4003.
<http://dx.doi.org/10.1021/cm8003276>
14. Koumura, N.; Wang, Z.-S.; Miyashita, M.; Uemura, Y.; Sekiguchi, H.; Cui, Y.; Mori, A.; Mori, S.; Hara K. *J. Mater. Chem.* **2009**, *19*, 4829–4836.
<http://dx.doi.org/10.1039/B905831A>
15. Zhang, X.-H.; Wang, Z.-S.; Cui, Y.; Koumura, N.; Furube, A.; Hara, K. *J. Phys. Chem. C* **2009**, *113*, 13409–13415.
<http://dx.doi.org/10.1021/jp808536v>
16. Zhang, X.-H.; Cui, Y.; Katoh, R.; Koumura, N.; Hara K. *J. Phys. Chem. C* **2010**, *114*, 18283–18290.
<http://dx.doi.org/10.1021/jp105548u>
17. Irgashev, R. A.; Karmatsky, A. A.; Kozyukhin, S. A.; Ivanov, V. K.; Sadovnikov, A.; Kozik, V. V.; Grinberg, V. A.; Emets, V. V.; Rusinov, G. L.; Charushin, V. N. *Synth. Met.* **2015**, *199*, 152–158.
<http://dx.doi.org/10.1016/j.synthmet.2014.11.024>
18. Liang, Y.; Peng, B.; Liang, J.; Tao, Z.; Chen, J. *Org. Lett.* **2010**, *12*, 1204–1207.
<http://dx.doi.org/10.1021/ol902973r>
19. Nishida, J. I.; Masuko, T.; Cui, Y.; Hara, K.; Shibuya, H.; Ihara, M.; Hosoyama, T.; Goto, R.; Mori, S.; Yamashita, Y. *J. Phys. Chem. C* **2010**, *114*, 17920–17925.
<http://dx.doi.org/10.1021/jp912047u>
20. Irgashev, R. A.; Karmatsky, A. A.; Rusinov, G. L.; Charushin, V. N. *Beilstein J. Org. Chem.* **2015**, *11*, 1000–1007.
<http://dx.doi.org/10.3762/bjoc.11.112>
21. Fuller, L. S.; Iddon, B.; Smith, K. A. *J. Chem. Soc., Perkin Trans. 1* **1997**, 3465–3470.
<http://dx.doi.org/10.1039/A701877K>
22. Nakayama, J.; Nakamura, Y.; Murabayashi, S.; Hoshino, M. *Heterocycles* **1987**, *26*, 939–942.
<http://dx.doi.org/10.3987/R-1987-04-0939>
23. Shi, J.; Chen, J. N.; Chai, Z. F.; Wang, H.; Tang, R. L.; Fan, K.; Wu, M.; Han, H. W.; Qin, J. G.; Peng, T. Y.; Li, Q. Q.; Li, Z. *J. Mater. Chem.* **2012**, *22*, 18830–18838.
<http://dx.doi.org/10.1039/C2JM33833E>
24. Hua, Y.; Chang, S.; Wang, H. D.; Huang, D. D.; Zhao, J. Z.; Chen, T.; Wong, W. Y.; Wong, W. K.; Zhu, X. J. *J. Power Sources* **2013**, *243*, 253–259.
<http://dx.doi.org/10.1016/j.jpowsour.2013.05.157>
25. Hua, Y.; Chang, S.; He, J.; Zhang, C.; Zhao, J.; Chen, T.; Wong, W.-Y.; Wong, W.-K.; Zhu, X. *Chem. -Eur. J.* **2014**, *20*, 6300–6308.

<http://dx.doi.org/10.1002/chem.201304897>

26. Sorohhov, G.; Yi, C.; Grätzel, M.; Decurtins, S.; Liu, S.-X. *Beilstein J. Org. Chem.* **2015**, *11*, 1052–1059.

<http://dx.doi.org/10.3762/bjoc.11.118>

27. Mishra, A.; Fischer, M.; Bäuerle, P. *Angew. Chem. Int. Ed.* **2009**, *48*, 2474–2499.

<http://dx.doi.org/10.1002/anie.200804709>

28. Clifford, J. N.; Martinez-Ferrero, E.; Viterisi, A.; Palomares, E. *Chem. Soc. Rev.* **2011**, *40*, 1635–1646.

<http://dx.doi.org/10.1039/B920664G>

29. Zhang, S.; Yang, X.; Numata, Y.; Han, L. *Energy Environ. Sci.* **2013**, *6*, 1443–1464.

<http://dx.doi.org/10.1039/C3EE24453A>