

Supplementary Material

Oxidation of N-doped multiwalled carbon nanotubes and formation of discontinuous spiraled carbon nanoribbons

Aman Preet Kaur, Mark S. Meier, Rodney Andrews and Dali Qian

^a*Department of Chemistry, University of Kentucky, Lexington, KY 40506-0055*

^b*Center for Applied Energy Research, University of Kentucky, Lexington, KY 40511-8479*

^c*Department of Chemical and Materials Engineering, University of Kentucky, Lexington, KY 40506-0046*

Email: meier@uky.edu

Table of Contents

1. Figure S1-S8	S2
2. Table S1	S5

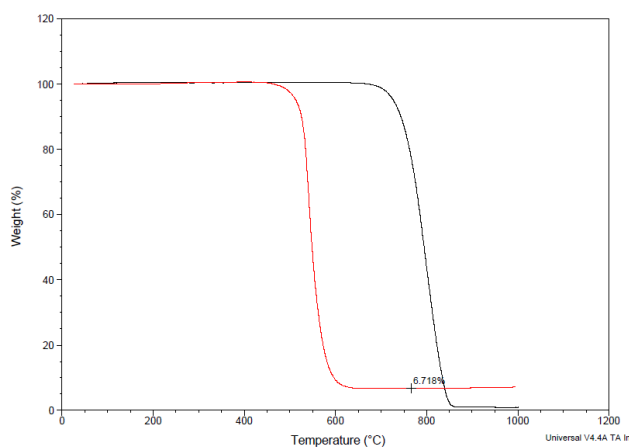


Figure S1. TGA plot comparing as-produced N-MWCNTs (red) with thermally annealed N-MWCNTs (G-N-MWCNTs).

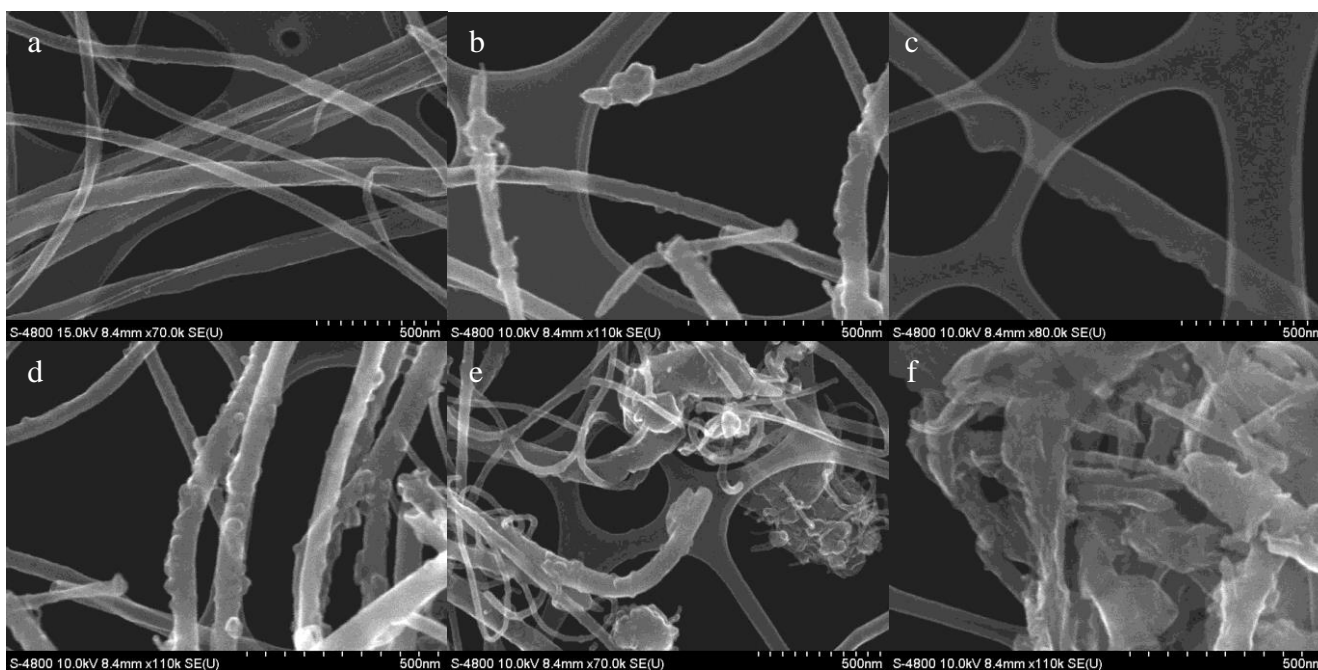


Figure S2. SEM images of G-N-MWCNTs treated with conc. HNO₃ after: a) 6h; b), and c) damages (surface etching and exfoliation) observed in few tubes after 6h; d) and e) 12h and f) 24h.

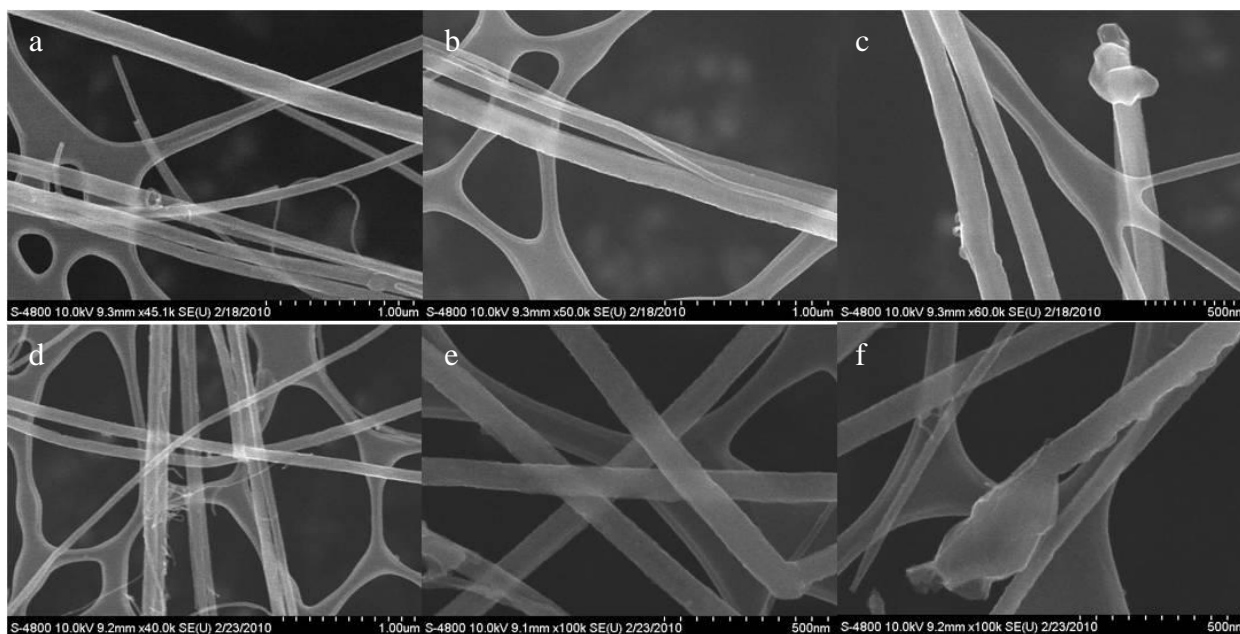


Figure S3. SEM images of G-N-MWCNTs treated with piranha solution after: a), b) & c) 12h ; d), e) & f) 24h.

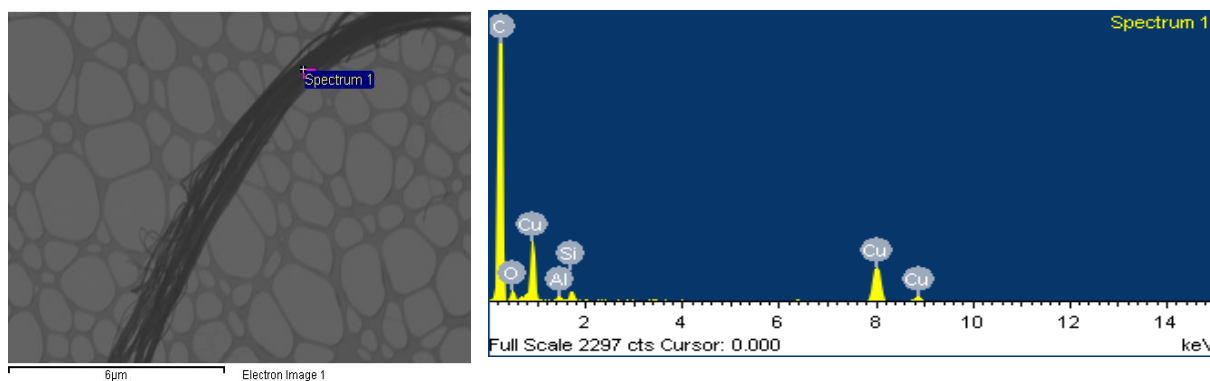


Figure S4. EDX on Fenton oxidized tube showed mostly carbon and no signs of Fe (Cu from Cu grid, Al from sample holder, small amounts of Si is residue from quartz tube furnace).

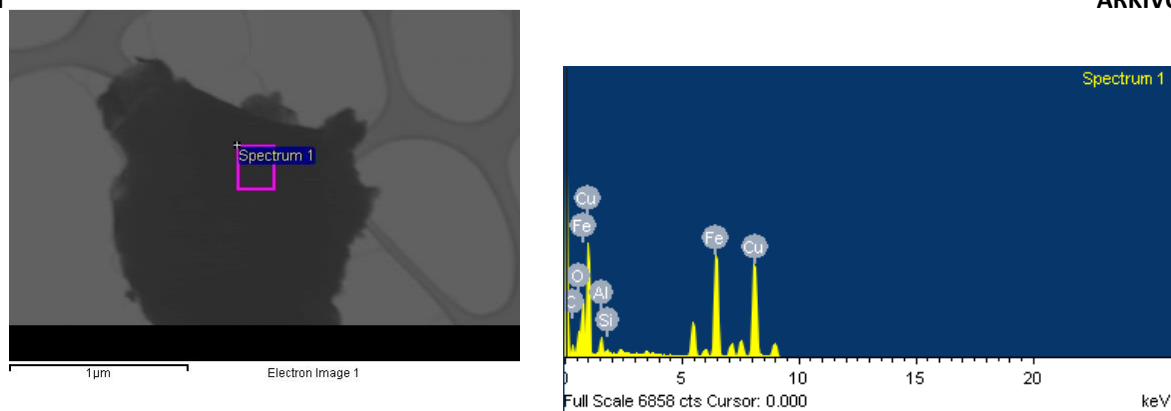


Figure S5. EDX on large fragments in Fenton oxidized tubes. (average carbon (16 %) signal may be from lacey carbon) (Cu from Cu grid, Al from sample holder, small amounts of Si is residue from synthesis, and small unlabeled peaks are Cr and Ca).

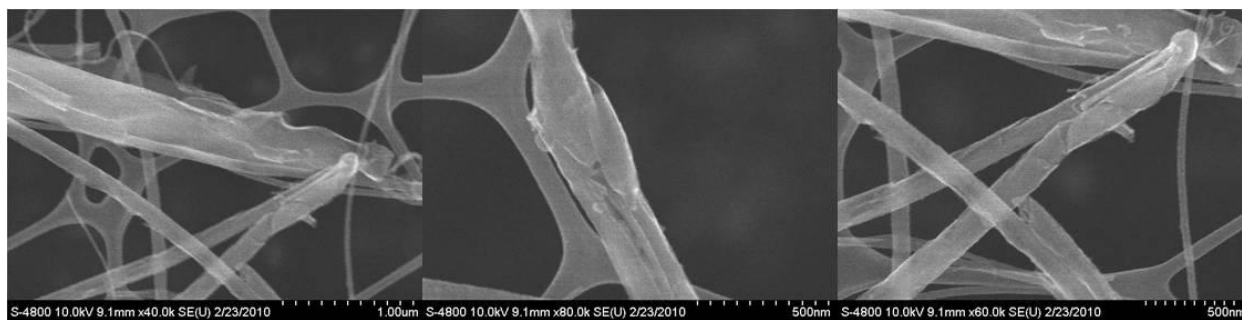


Figure S6. SEM images of G-N-MWCNTs treated with $\text{H}_2\text{SO}_4/\text{HNO}_3$ (stirring for 24h).

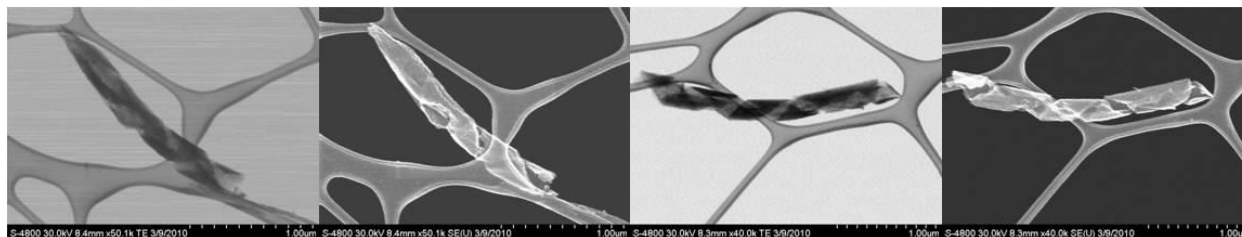


Figure S7. STEM and SEM images of G-N-MWCNTs treated with $\text{H}_2\text{SO}_4/\text{HNO}_3$ (sonication for 24h).

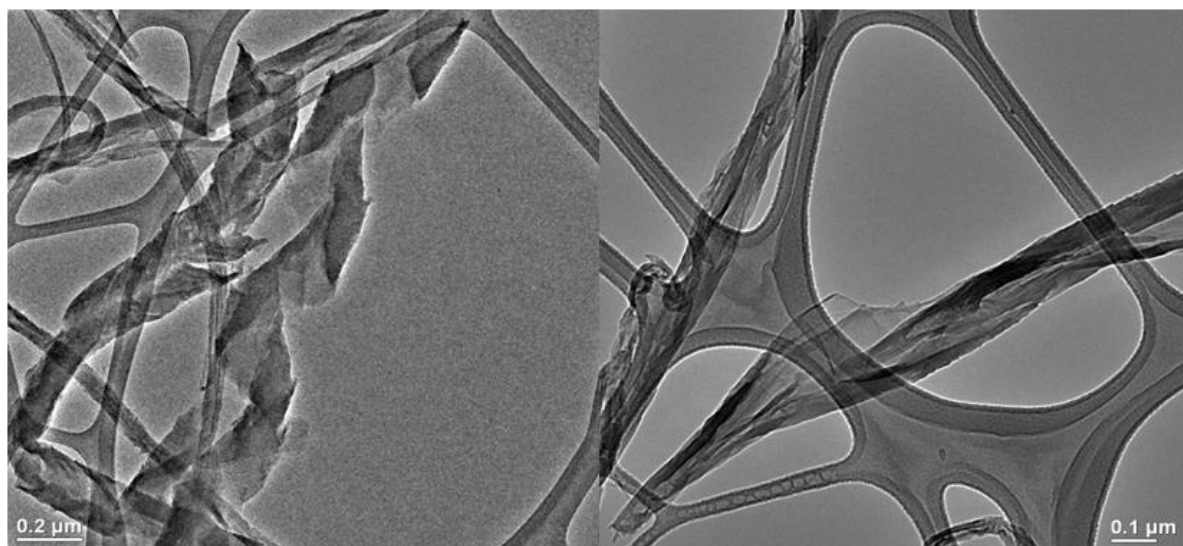


Figure S8. TEM images of $\text{KMnO}_4/\text{H}_2\text{SO}_4$ oxidized G-N-MWCNTs.

Table S1. Table reporting onset temperature of oxidation, temperature of maximum rate of oxidation and % residue (residue is because of Si, which is believed to be present in starting tubes during their synthesis).

Sample	Onset temperature of oxidation of remaining carbon ($^{\circ}\text{C}$)	Temperature of maximum rate of oxidation ($^{\circ}\text{C}$)	Wt. % residue
G-N-MWCNTs	666	795	2.5%
HNO_3 oxidized 6h	584	763	2.5%
HNO_3 oxidized 12h	576	758	2.5%
HNO_3 oxidized 24h	557	733	2.5%
Piranha oxidized 12h	666	795	2.5%
Piranha oxidized 24h	646	782	2.5%
Fenton oxidized	577	724	2.5%
$\text{H}_2\text{SO}_4/\text{HNO}_3$ oxidized 12h	558	704	1.3%
$\text{H}_2\text{SO}_4/\text{HNO}_3$ oxidized 24h	530	682	1.3%
$\text{KMnO}_4/\text{H}_2\text{SO}_4$ oxidized	510	583	1%