

## Synthesis of poly(vinyl ether)s by chain-end capping with a silyl ketene acetal in *ab initio* cationic polymerisations

Prodip Sarker,<sup>a</sup> Weihong Lang,<sup>a</sup> Rami Obaid,<sup>a</sup> and Stephen Rimmer<sup>b\*</sup>

<sup>a</sup>Department of Chemistry, University of Sheffield, Sheffield, South Yorkshire, UK, S3 7HF

<sup>b</sup>Polymer and Biomaterials Chemistry Laboratories, School of Chemistry and Biosciences, University of Bradford, Bradford, West Yorkshire, UK, BD7 1DB

E-mail: [s.rimmer@bradford.ac.uk](mailto:s.rimmer@bradford.ac.uk)


Received 04-16-2021

Accepted Manuscript 05-19-2021

Published on line 06-04-2021

### Abstract


Inclusion of a silyl ketene acetal in the non-living cationic polymerisations of methyl and *isobutyl* vinyl ether provides polymers with ester end groups. The use of an *ab initio* approach produces materials with high degrees of chain end functionality provided the reaction temperature, monomer concentration and concentration of silyl ketene acetal are optimised. Optimisation, studied mainly by the use of MALDI-ToF mass spectrometry, involved obtaining reaction conditions in which the dominant termination reaction was alkylation of the silyl ketene acetal then rapid desilylation produced the ester end groups.

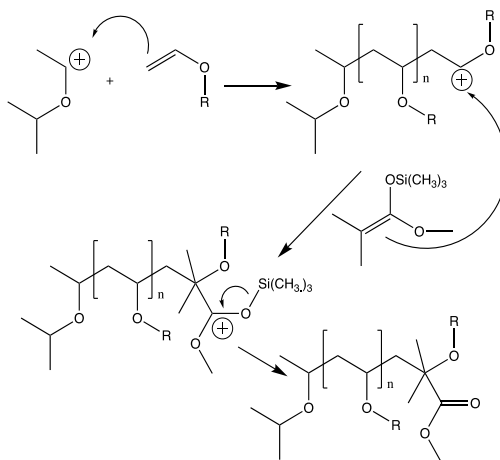

**Keywords:** Cationic polymerisation, vinyl ether, silyl ketene acetal, ester end group

## Introduction

End functional polymers are ubiquitous in many important established technologies (e.g. adhesives and paints.) and the newer emergent technologies (drug delivery, controlled release etc.). They are precursors to a wide variety of classes of materials including polymer networks,<sup>1</sup> polymer brushes<sup>2,3</sup> and block copolymers.<sup>4</sup> The end groups can provide interesting solution and bulk properties.<sup>5</sup> In step growth polymerisations the required chain end functionality can easily be added by stopping the polymerisation at moderate extent of reaction or by carrying out polymerisations at non-equivalent stoichiometry. On the other hand, addition of end group functionality in chain growth polymerisations requires control of the termination processes. During radical chain growth polymerisation chain end functionality can be added in a number of ways: by capping the chains produced in controlled polymerisations; using transfer processes or by controlled cleavage of high molecular weight polymers.<sup>6</sup> In ionic polymerisations the only generally practiced method is the chain end capping of sequential living polymerisations, which requires the propagating chain end to remain active until a functional terminating agent is added in a separate step.<sup>7-12</sup> However, an alternative method uses the discovery that, in both the cationic polymerisation of vinyl ethers and conventional radical polymerisations, it was possible to add species (silyl enol ethers), which terminate the propagating chain and add chain end functionality simultaneously with propagation.<sup>13-16</sup>

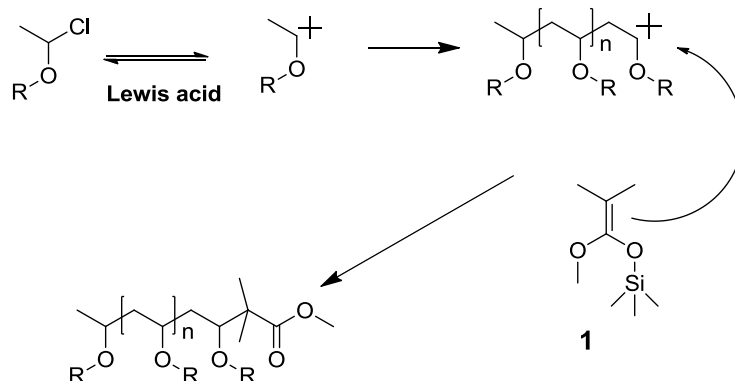

**Scheme 1.** Polymerisation of vinyl ethers in the presence of 1-methoxy-2-methyl-1-(trimethylsilyloxy)propene, (1).


In cationic polymerisations we used the term *ab initio* cationic polymerisation to distinguish these polymerisations from living cationic polymerisation approaches that involve addition of the nucleophilic capping agent after propagation had finished.<sup>13</sup> The method has the advantage, in that it is applicable to polymerisations with short cation or radical lifetimes: i.e. the chain capping reaction competes with the normal termination reactions and occurs on the same timescale as propagation so that living polymerisation is not required. Optimisation of these polymerisations produced polymers with essentially 100% of the chain end functionality produced by the alkylation of the added silyl enol ether. In the case of the use of silyl enol ethers Sawamoto *et al* had previously shown that the reaction of silyl enol ethers at the end of living cationic polymerizations produced polymers with the same high degree of chain end functionality but their use of living polymerizations required careful control of reactant purity, exclusion of water, etc.<sup>17-21</sup> Chain-end capping to provide polymers with useful end group functionality was recently reviewed by Tasdelen *et al*<sup>22</sup> and as far as we are aware there is only one example of the use of the reactions of silyl ketene acetals with polymer carbocations in chain capping reactions involving living polymerizations of vinyl ethers.<sup>21</sup> The

alkylation of silyl ketene acetals with carbocations produces esters<sup>23-25</sup> that would be of general utility in the production of polymers with a wide variety of useful end groups. Also, silyl ketene acetals are highly nucleophilic and the reactivity scales produced by Mayr indicated that they would have suitable rate constants for use as terminating agents during *ab initio* cationic polymerisation.<sup>24,25</sup> Therefore, in this work we report that the modification of the cationic polymerizations of vinyl ethers, methyl vinyl ether (MVE) and *isobutyl* vinyl ether (*i*BVE) with a commercially available silyl enol ketal, 1-methoxy-2-methyl-1-(trimethylsilyloxy)-propene, **1**, produces polymers with useful ester end groups, as shown in scheme 1. Both SnCl<sub>4</sub> and TiCl<sub>4</sub> have been used for the polymerisation of *i*BVE) and they can be used as Lewis acids without additives.<sup>32</sup> However, SnCl<sub>4</sub> living polymerisation was only observed at low concentration (5 x 10<sup>-4</sup> mol. dm.<sup>-3</sup>) and at low temperature (-78 °C rather than -15 °C).<sup>32</sup> The use of TiCl<sub>4</sub> in the polymerisation *i*BVE provided a living polymerisation at -78 °C but MALDI-TOF mass spectrometry showed that significant transfer occurred at -15 °C leading to initiation by H<sup>+</sup>. The rates of polymerisation with strong Lewis acids are often very fast and in systems that require sequential capping of living polymers the long residence time (compared to the time for propagation) of the living chain, in contact with Lewis acid but at low monomer concentration, can lead to side reactions after propagation has finished. Chain capping with agents added at the start of the polymerisation can be used to alleviate this problem because the rate of chain capping is similar to the rate of propagation and this minimises the lifetime required for the carbocationic chain end.

## Results and Discussion

### Polymerisations of methyl vinyl ether

Initially, polymerisations of MVE were attempted using SnCl<sub>4</sub> as Lewis acid. However, typically, living polymerisation of MVE with SnCl<sub>4</sub> as Lewis acid requires the use of modifiers, such as tetraalkyl ammonium salts.<sup>29</sup> In this work no modifiers were used and it was found that it was not possible to produce polymers with high degrees of chain end functionality with this Lewis acid at either -26 or -78 °C. The MVE polymers were also highly disperse in molar mass.

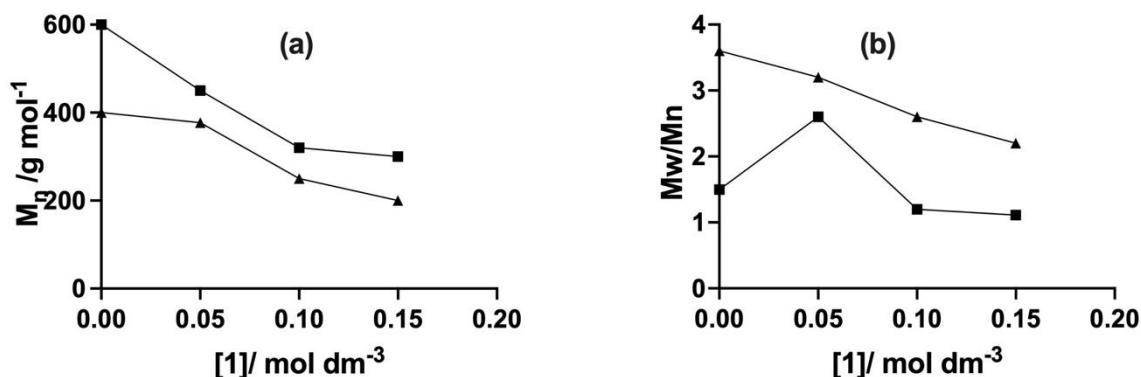


**Figure 1.** Molar mass (SEC) data for polymerisation of MVE (0.6 mol dm<sup>-3</sup>) in the presence of **1** initiated by *i*BVE:HCl:TiCl<sub>4</sub> (0.05 mol dm<sup>-3</sup>). Reaction time 1.5 hours at -26 °C ■ or -78 °C ▲.

Following these experiments the polymerisations of MVE were carried out using *i*BVE:HCl:TiCl<sub>4</sub> as initiator at -26 and -78 °C in the presence of **1**. Some polymerisations were also conducted at -15 °C but MALDI-ToF

mass spectrometry showed that these polymerisations produced polymers with a multitude of chain ends and no further work was carried out at this temperature.


A series of polymerisations were carried out in which the starting initiator and monomer concentrations were held constant but the concentration of **1** was varied. The data from these experiments are presented in figures 1, 2 and 3. Alkylation of silyl enol ethers during the timescale for propagation leads to a reduction in the degree of polymerisation as the concentration of the terminating agent changes. Alternatively, propagation that is much faster than alkylation is analogous to a conventional living polymerization, in which the degree of polymerisation is independent of the concentration of a capping agent. Thus, evidence for capping of the carbocationic chain end during propagation was derived from plots of molar mass against **1**, as shown in Figure 1(a) that is, at both polymerisation temperatures, molar mass decreases sharply as the initial concentration of **1** increases. In figure 1(b) Control of the termination reactions was also indicated by decreasing dispersity ( $M_w/M_n$ ). One factor that produces broadening in  $M_w/M_n$  in a non-living cationic polymerization is the existence of several routes to chain termination. If alkylation of **1** is the dominant termination reaction the system becomes subject to a single termination rate constant, which decreases  $M_w/M_n$ . Figure 1(b) shows that there was a general decrease in  $M_w/M_n$  as the concentration of **1** increased at both polymerisation temperatures. However, at  $-26^\circ\text{C}$  there was an increase in  $M_w/M_n$  compared to the result obtained in the absence of **1** when it was added at an initiator:**1** ratio of 1:1 ( $[\mathbf{1}] = 0.05 \text{ mol dm}^{-3}$ ). Further increases in  $[\mathbf{1}]$  lead to a substantial decrease in  $M_w/M_n$ . At  $-78^\circ\text{C}$  the normal termination processes led to a high value of  $M_w/M_n$  in the absence of **1**. However, as expected, as  $[\mathbf{1}]$  increased  $M_w/M_n$  decreased as the rate of alkylation increased to become the dominant termination process.

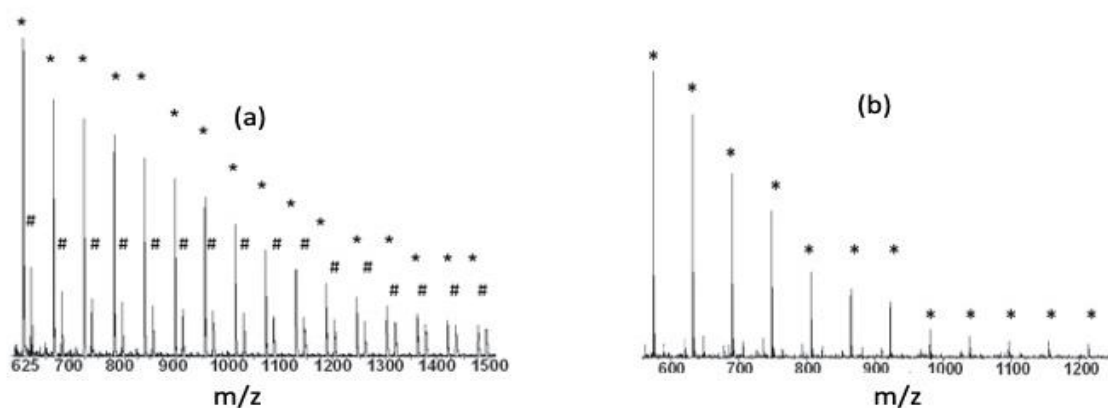

**Figure 2.** MALDI ToF mass spectra derived from: (a) MVE polymerised at  $-26^\circ\text{C}$  (b) MVE polymerised at  $-78^\circ\text{C}$  ( $[\mathbf{1}] = 0.15 \text{ mol. dm}^{-3}$ ). Ion series indicated with \* or #.


It is possible to use MALDI-ToF mass spectrometry to calculate chain end functionality if it is assumed that at constant degree of polymerisation the influence of the end groups on the extent of ionisation is not significant. Figure 2(a) derived from polymerisation at  $-26^\circ\text{C}$  ( $[\mathbf{1}] = 0.15 \text{ mol. dm}^{-3}$ ) contains two series of ions,  $m/z = n58.0 + (23.0 + 202.3)$ , which are derived from cationisation by sodium, and  $m/z = n58.1 + (23.0 + 102.1)$ , which are derived from the polymers with methyl-(2, 2 dimethyl) ethanoate at the  $\omega$ -end but the methoxy ethyl group at the  $\alpha$ -chain end. The latter group would be obtained from initiation by  $\text{H}^+$  from adventitious water or from termination by elimination. The former is more likely given that the spectra do not include any series that could be assigned to polymers derived from elimination. Figure 2(b) shows a mass

spectrum produced from a polymerisation carried out at  $-78^{\circ}\text{C}$  ( $[\mathbf{1}] = 0.15 \text{ mol. dm}^{-3}$ ). The dominant distribution was composed of ions separated by  $m/z$  58 and the distribution could be described by  $m/z = (58n + 23 + 202)$ . Thus, both spectra were derived from polymer ions with end groups that sum to  $m/z$  202; i.e. 1-*isobutoxy* ethyl at the  $\alpha$ -end and methyl-(2, 2 dimethyl) ethanoate at the  $\omega$ -end. The spectra show that polymers produced using this procedure produced almost entirely the target species and as expected there was little evidence for polymers that were initiated by  $\text{H}^+$  at  $-78^{\circ}\text{C}$ .

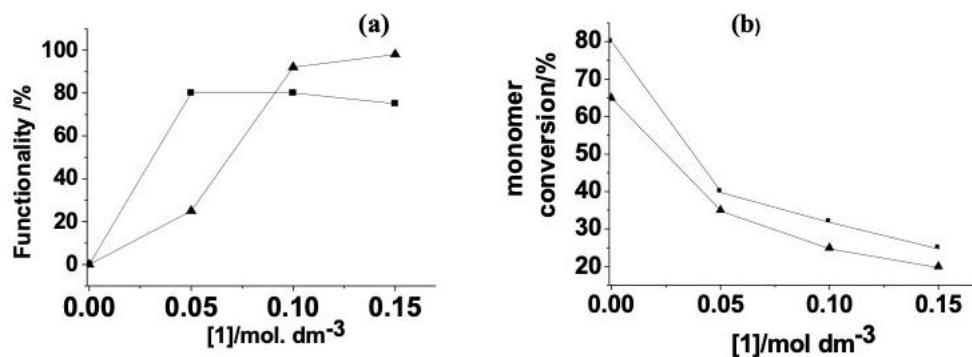

**Figure 3.** (a) Functionality (percentage of chain ends derived from alkylation of **1**) of polyMVE prepared with various initial  $[\mathbf{1}]$ .  $-26^{\circ}\text{C}$  ■ or  $-78^{\circ}\text{C}$  ▲; (b) MVE conversions after 1.5 hours prepared with various initial  $[\mathbf{1}]$ .  $-26^{\circ}\text{C}$  ■ or  $-78^{\circ}\text{C}$  ▲.

Katayama *et al*<sup>32</sup> had previously shown that polymerisation of *i*BVE initiated with  $\text{TiCl}_4$  was living at  $-78^{\circ}\text{C}$  and the data reported here showed that the polymerisation of MVE using  $\text{TiCl}_4$  could be modified by addition of **1** at  $-78^{\circ}\text{C}$  to provide polymers with the target ester end groups. On the other hand as stated previously it was not possible to produce poly(MVE) with high end group functionality using  $\text{SnCl}_4$  as Lewis acid. Functionalities (ie the mole percent with  $\alpha$ -1-*isobutoxy* ethyl,  $\omega$ -methyl-(2, 2 dimethyl) ethanoate chain ends) were calculated from the MALDI ToF mass spectra<sup>15</sup> and the data are presented in figure 3(a). At  $-78^{\circ}\text{C}$ , the polymerisations carried out at  $[\mathbf{1}] = 0.05 \text{ mol. dm}^{-3}$  (1:1 molar equivalence of **1**:initiator) gave lower degrees of functionality than polymerisations run with excess **1**. However, as indicated in figure 3(a) and shown earlier in figure 2(b) the polymerisation carried out at  $-78^{\circ}\text{C}$  and  $[\mathbf{1}] = 0.15 \text{ mol. dm}^{-3}$  produced chains that contained only negligible amounts of ends other than those derived from the initiator and **1**. The polymerisations at  $-26^{\circ}\text{C}$  produced polymers that were partially functionalised by the initiator and **1** at all concentrations of **1**. The data indicated that at  $-26^{\circ}\text{C}$  the alkylation of **1** was the main termination reaction but the target polymer, with 1-*isobutoxy* ethyl at the  $\alpha$ -end and methyl-(2, 2 dimethyl) ethanoate at the  $\omega$ -end, was only produced in 80% yield. The other 20% of the product, as shown in figure 2a was derived from initiation by  $\text{H}^+$  derived from adventitious water. At  $-78^{\circ}\text{C}$  the alkylation of **1** dominated the termination processes in the presence of excess **1**.

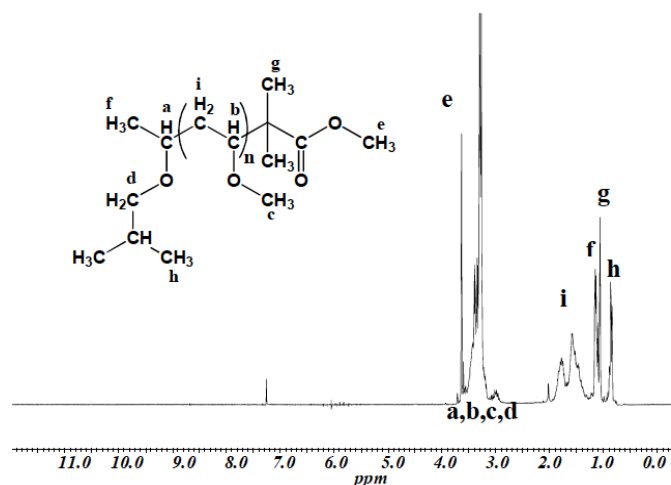


**Figure 4.**  $^1\text{H}$  NMR spectrum of PMVE prepared at  $-26\text{ }^\circ\text{C}$  in the presence of **1**. Assignments at a,b,c,d and i are described in reference 26.

In this work one of our aims was to alleviate the need to resort to excessive purification and drying of reagents, monomers and solvents so that in this respect these polymerisations are clearly best carried out at  $-78\text{ }^\circ\text{C}$  rather than  $-26\text{ }^\circ\text{C}$  because at  $-26\text{ }^\circ\text{C}$  adventitious water can initiate undesirable polymerisations leading to polymers with unwanted chain end functionalities. Figure 3(b) shows that as expected the increased rates of termination, which are inevitable as **[1]** increases, led also to a decrease in final monomer conversion. Although this is clearly a disadvantage in a batch polymerisation we consider that future developments of this method will require the use of a semi-continuous process in which initiator is replenished throughout the time course of the polymerisation. A similar approach was used by us recently in radical polymerisations carried out in the presence of a silyl enol ether.<sup>16</sup>

Figure 4 shows a representative  $^1\text{H}$  NMR spectrum from a MVE polymerisation. In all of the examples of polymerisations, carried out in the presence of **1**, resonances from the methyl groups at position **g** were observed at 1.05 ppm and the methyl groups at positions **f** and **h** were observed as indicated in the figure. The methoxy group was also observed at 3.70 ppm (**e** in figure 4). The peak at **g** and **e** were both absent from analogous polymerisations carried out in the absence of **1**.  $^{13}\text{C}$  NMR spectra also showed two resonances at 177 and 178 ppm that were assigned to the chain end ester carbonyl group.


### Polymerisations of *isobutyl* vinyl ether

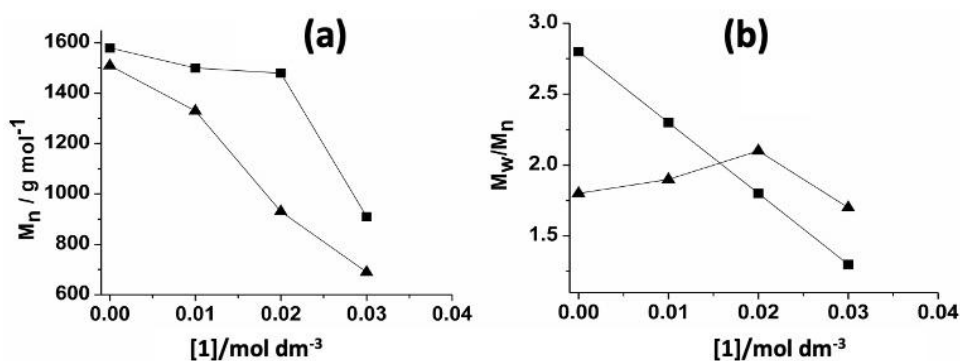

**Figure. 5** Molar mass data for polymerization of *i*BVE (1.0 mol dm<sup>-3</sup>) in the presence of **1** initiated by *i*BVE:HCl:SnCl<sub>4</sub> (0.01 mol dm<sup>-3</sup>). Reaction time 1.5 hours at -26 °C ■ or -78 °C ▲.


It is known that the polymerisation of MVE and other vinyl ethers progress with different rate constants for initiation propagation and termination<sup>27,28</sup> and these differences were expected to be reflected in the results from *i*BVE polymerisation compared to polymerisation of MVE in the presence of **1**. Figure 5 shows molar mass data from polymerisations using SnCl<sub>4</sub> as Lewis acid. The results show that  $M_n$  decreased with increasing **1** at both -26 and -78 °C. Figure 5b) shows that at -78 °C  $M_w/M_n$  increased with increasing **1** upto 0.02 mol. dm<sup>-3</sup> but then decreased. On the otherhand  $M_w/M_n$  decreased continuously as **1** increased when the polymerisations were carried out at -26 °C. Therefore, the data provide indications that capping of the chain end occurred within the timescale of propagation but the increase in  $M_w/M_n$  provided indications that multiple termination and/or initiation mechanisms were operative.

Examples of the MALDI-ToF mass spectra from polymers produced at -26 and -78 °C are shown in figure 6. Both spectra were composed of a dominant series of ions that were described by: 6(a), reaction temperature -26 °C  $m/z = n99.7 + (23 + 201.7)$  and 6(b), reaction temperature -78 °C  $m/z = n99.8 + (23+202.7)$ . The end groups of these series of ions were thus composed of the predicted  $\alpha$ -H and  $\omega$ -methyl-(2, 2 dimethyl) ethanoate moieties. In figure 6(a) (reaction temperature = -26 °C) a significant secondary series of ions was observed that was described by  $m/z = n99.7 + (23 + 74)$ . The end masses of this series can be rationalised as being derived from by chain ends that were capped with H at  $\alpha$  and *isobutoxy* at  $\omega$ , as observed in previous polymerisations with this monomer.<sup>30</sup> In figure 6(b) (reaction temperature = -78 °C) another minor series described by  $m/z = n100.0 + (23 + 45.3)$  was observed. This mass correlates to the end groups with H at the  $\alpha$  chain end and -CH<sub>2</sub>CHO at the  $\omega$  chain end. Poly(*i*BVE) with -CH<sub>2</sub>CHO end group has been previously observed using MALDI ToF mass spectrometry by Katayama et al.<sup>31</sup> Figure 7a shows how the functionality of these polymers increased to approximately 75%, as the concentration of **1** was increased. In similar polymerisations of MVE using SnCl<sub>4</sub> it was only possible to produce polymers with a maximum of 60% functionality (at -78 °C). Clearly, this system requires further optimisation but the data do indicate that useful poly(*i*BVE)s with ester end groups can be produced in this way.

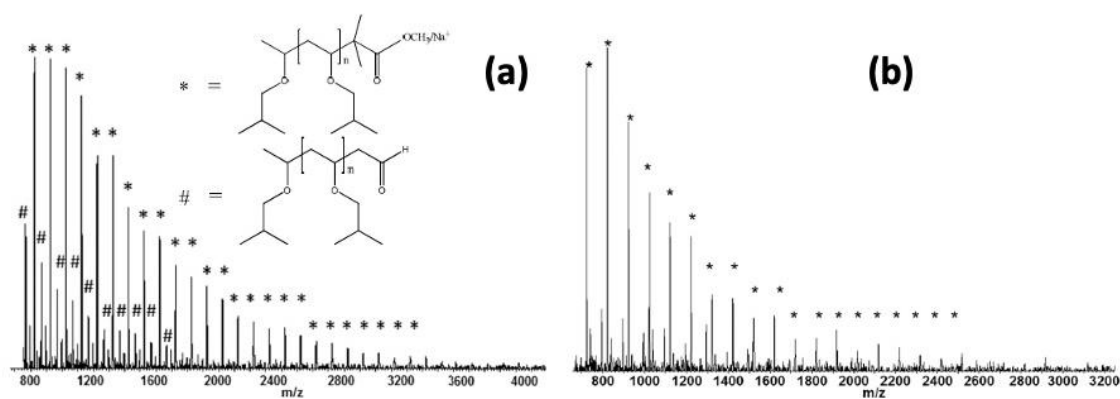

**Figure 6.** MALDI ToF mass spectra derived from: (a) *i*BVE polymerised at -26 °C (b) *i*BVE polymerised at -78 °C ( $[i\text{BVE}] = 1.0 \text{ mol dm}^{-3}$ ,  $[i\text{BVE}:\text{HCl}:\text{SnCl}_4] = 0.01 \text{ mol dm}^{-3}$ ,  $[1] = 0.03 \text{ mol. dm}^{-3}$ ). Ion series indicated with \* or #.



Figure 7(b) shows that, as expected the final monomer conversion decreased as  $[1]$  was increased. As discussed for MVE the decrease in both  $M_n$  and final conversion with increasing  $[1]$  provide good evidence for alkylation of **1** on the same timescale as propagation rather than alkylation that occurs after propagation.

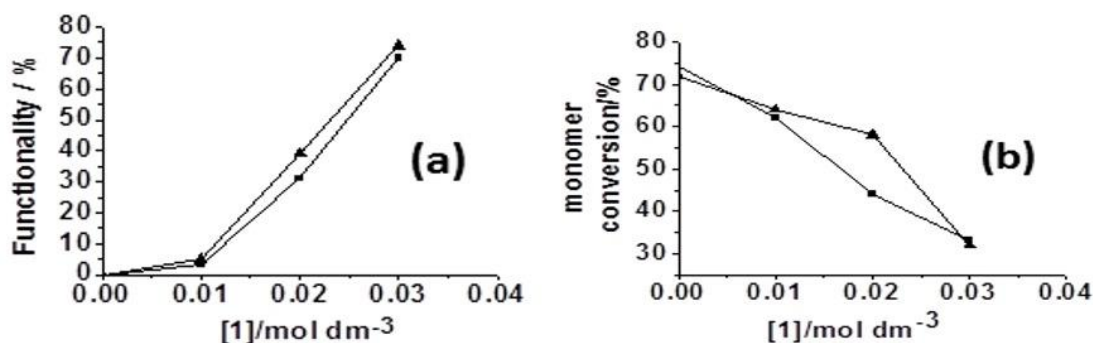

**Figure 7.** (a) Functionality of poly(*i*BVE) prepared with various initial  $[1]$ . (b) *i*BVE conversions for polymerization of *i*BVE ( $1.0 \text{ mol dm}^{-3}$ ) in the presence of **1** initiated by *i*BVE:HCl:SnCl<sub>4</sub> ( $0.01 \text{ mol dm}^{-3}$ ). Reaction time 1.5 hours at -26 °C ■ or -78 °C ▲.


Further optimisation of the polymerisation of *i*BVE was carried out using an initial concentration of  $0.38 \text{ mol dm}^{-3}$  at -78, -15, 0 and 20 °C. MALDI-ToF mass spectra from these polymerisations are shown in figure 8. At -78 °C, the dominant ion distribution in these data was described by  $m/z = n100.1 + (23 + 202.2)$  and this distribution amounted to more than 95% of the chains. Figure 8 also shows spectra from other reaction temperatures and at -15, 0 or 20 °C significant fractions of the ions were derived from distributions of chains with other end groups. Notably at 20 °C the distribution from the target ions, with H at the  $\alpha$ -end and methyl-(2, 2 dimethyl) ethanoate at the  $\omega$ -end, was a minor component of the overall mass spectrum. At 20 °C the major distribution of ions was  $m/z = n100.1 + (23 + 146.1)$  or  $(23 + 46.1)$ , which (as previously reported<sup>30</sup>) can be assigned to polymers with -CH<sub>2</sub>CH<sub>2</sub>OH and -H groups at the  $\omega$  and  $\alpha$ -chain ends respectively. Also, at -15 and 0 °C other distributions of ions were observed that were described by  $m/z = 100.2 + (23 + 74.3)$  and  $m/z = n100.0 + (23 + 29.3)$ . Both of these ion series have been assigned previously by us and are derived from chain ends that are capped with the *isobutoxy* and *methoxy* groups respectively.<sup>30</sup>



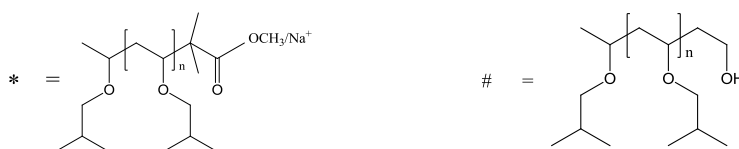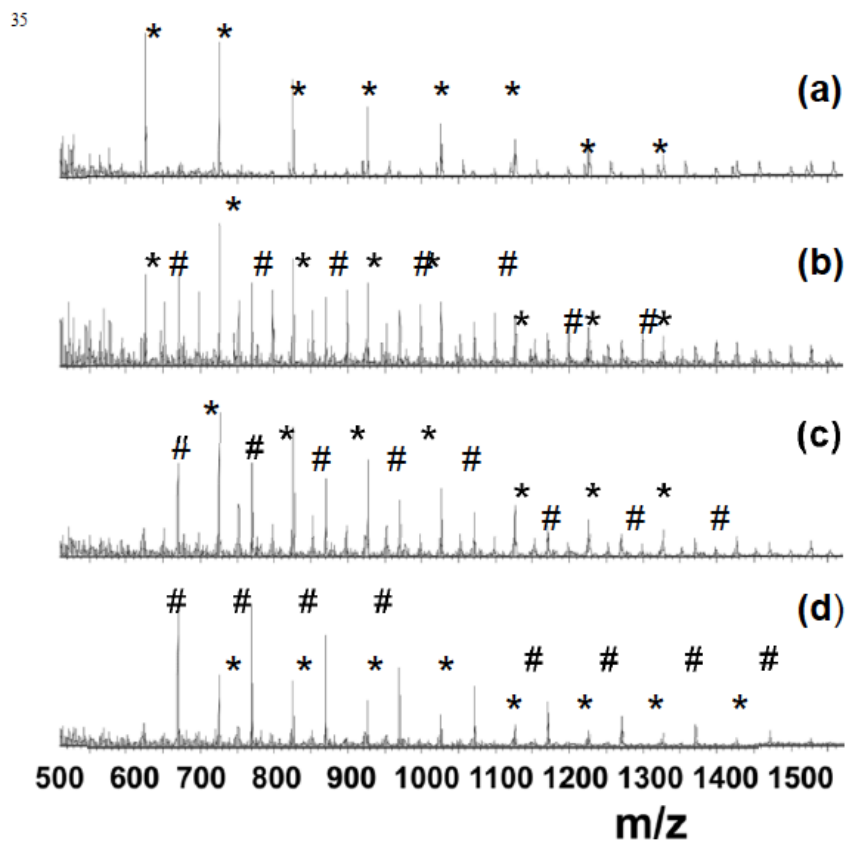


**Figure 8.** MALDI ToF mass spectra for polymerization of *i*BVE (0.38 mol. dm<sup>-3</sup>) in the presence of **1** initiated by *i*BVE:HCl:SnCl<sub>4</sub> (0.038 mol. dm<sup>-3</sup>). Reaction time 1 hour. Polymerisation temperatures:(a) -78 ; (b) -15; (c) 0 and (d) 20 °C. Ion series indicated with \* or #.

*Ab initio* cationic polymerisations of *i*BVE in the presence of TiCl<sub>4</sub> as a Lewis acid were carried out at -26 and -78 °C with differing concentrations of **1**. The resultant molar masses and dispersities are shown in Figure 9.

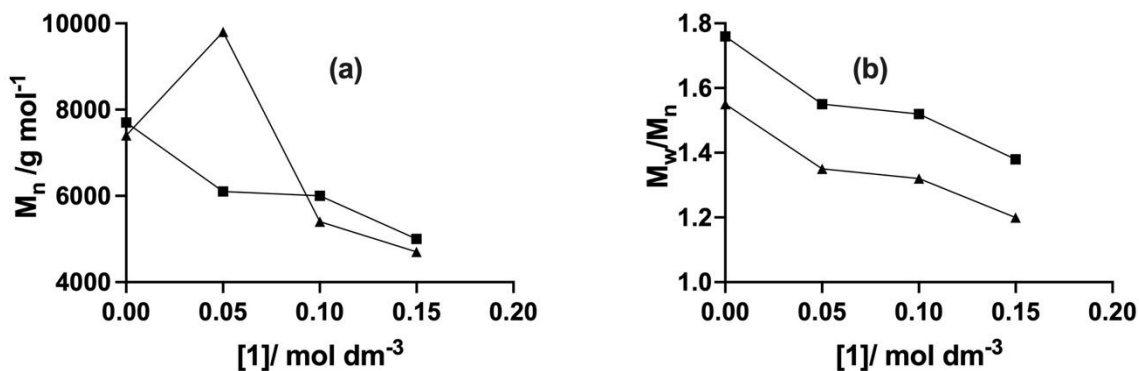


**Figure 9.** Molar mass (SEC) data for polymerisation of *i*BVE (1.0 mol dm<sup>-3</sup>) in the presence of **1** initiated by *i*BVE:HCl:TiCl<sub>4</sub> (0.01 mol dm<sup>-3</sup>). Reaction time 1.5 hours at -26°C ■ or -78°C ▲.


Figure 9 shows that at both -26 and -78 °C  $M_n$  was reduced as  $[1]$  increased. However, unexpectedly there was an increase at a molar ratio of initiator:**1** of 1:5 at -78 °C. An increase in  $M_n$  would occur in this system if the concentration of initiator was reduced as initiator reacted with **1** in a similar time frame to addition to the monomer alkene group. However, the data suggest that at higher concentrations of **1** the rate of alkylation of **1** by the propagating chain increased and  $M_n$  decreased. On the otherhand Figure 9b showed that the dispersity in molar mass reduced as  $[1]$  was increased, as expected in polymerisations in which alkylation of  $[1]$  occurred in the same timescale as propagation. A typical <sup>1</sup>H nmr spectrum is shown in Figure 10. The spectra provided evidence for the α-H and the methyl groups from the ω-methyl-(2, 2 dimethyl) ethanoate between 1 and 1.2 ppm. Also, the methoxy moiety from this end group was observed at 3.70 ppm.

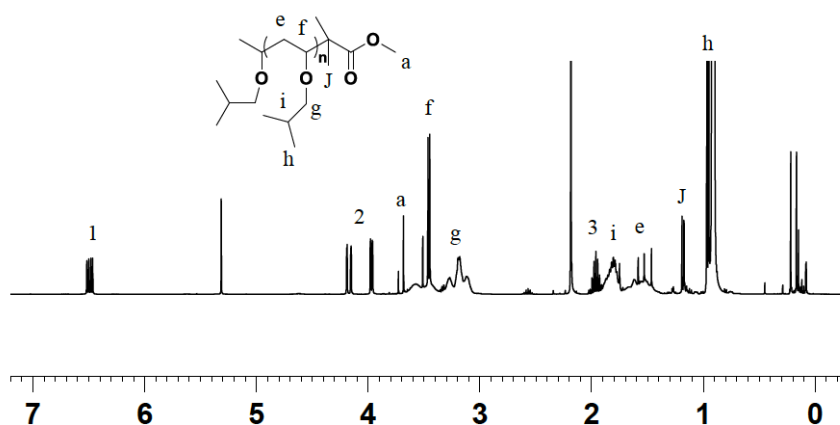

**Figure 10.** A Typical <sup>1</sup>H NMR spectrum of poly*i*BVE synthesised in the presence of **1**. Peaks 1,2 and 3 are from residual monomer.

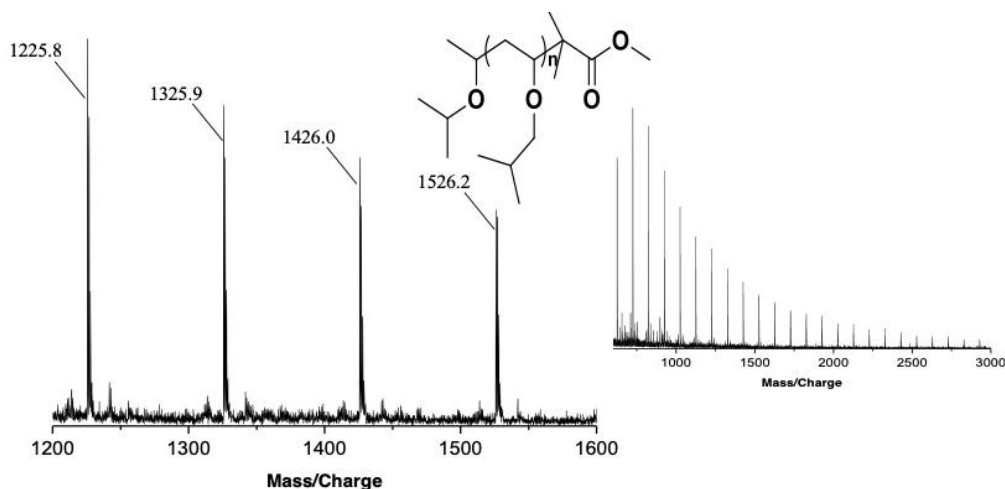

**Figure 11.** MALDI-TOF-MS spectrum with the determined chain end groups for poly(*i*BVE)  $0.15 \text{ mol. dm}^{-3}$  obtained by dried droplet method using Dithranol as a matrix, sodium iodide as salt and THF as the carrier solvent.

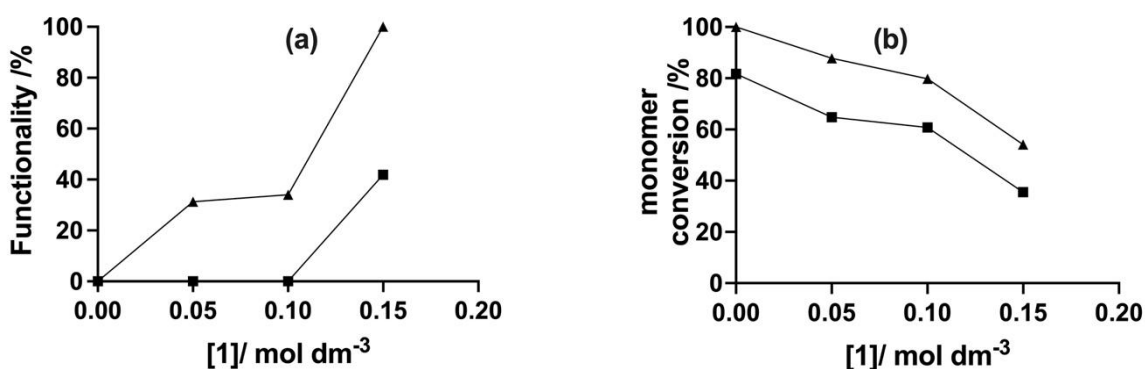

**Figure 12.** (a) Functionality of poly(*i*BVE) prepared with various initial **1**. (b) *i*BVE conversions for polymerisation of *i*BVE ( $1.0 \text{ mol. dm}^{-3}$ ) in the presence of **1** initiated by *i*BVE:HCl:TiCl<sub>4</sub> ( $0.01 \text{ mol. dm}^{-3}$ ). Reaction time 1.5 hours at  $-26^\circ\text{C}$  ■ or  $-78^\circ\text{C}$  ▲.

From Figure 12 it is clear that addition of **1** at  $-26^\circ\text{C}$  did not result in functionalisation of the chain ends, although 40% of the chain ends were found to be functionalised at  $[\mathbf{1}] = 0.15 \text{ mol dm}^{-3}$ . Functionalisation was much more effective at  $-78^\circ\text{C}$  because the rates of termination by elimination are much reduced at lower temperatures. The final monomer conversions are shown in Figure 12b and as expected the monomer conversions decreased as  $[\mathbf{1}]$  was increased.

## Conclusions

Poly(vinyl ether)s have been prepared with ester end groups using non-living *ab initio* cationic polymerisations, in which alkylation of a silyl ketene acetal occurred simultaneously with propagation. It was shown that optimisation of the reaction temperature, monomer concentration and concentration of the silyl ketene acetal was required to achieve high degrees of chain end functionality. However, provided these

parameters were carefully considered it was possible to produce reactive polymers with useful ester end groups in high yield and with almost all of the end groups containing the ester moiety. For the polymerisation of both MVE and *i*BVE it was found that high end group functionalities were obtained in polymerisations carried out at  $-78\text{ }^{\circ}\text{C}$  using  $\text{TiCl}_4$  as Lewis acid. Poly*i*BVE could also be prepared using  $\text{SnCl}_4$  as Lewis acid at a monomer concentration of  $0.38\text{ mol dm}^{-3}$  but at  $1.0\text{ mol dm}^{-3}$  chains with only as maximum of 70% esters at the chain ends were produced.

## Experimental Section

**General.** MVE (98% Aldrich) was purified by passing the gaseous monomer through a calcium hydride column and condensed at  $-80\text{ }^{\circ}\text{C}$ . *i*BVE (99%, Aldrich) was dried overnight with anhydrous sodium sulphate and distilled before use. N-hexane (99%, Aldrich) was refluxed over calcium hydride for two hours and distilled just before use. Sulphuric acid (concentrated) and sodium chloride (AR grade, BDH) were used as received. Dichloromethane (DCM) (99.6%, Aldrich) was refluxed over  $\text{CaH}_2$  and then distilled just before use.  $\text{SnCl}_4$  and  $\text{TiCl}_4$  ( $1.0\text{ mol. dm}^{-3}$  solution in DCM, Aldrich) were used as received. 1-methoxy-2-methyl-1-(trimethylsilyloxy)propene, **1**, (95%, Lancaster) was purified by fraction distillation under reduced pressure.

### Synthesis of HCl-*i*BVE adduct

The reaction was carried out in a pre-sealed three-neck round bottom flask under dry nitrogen atmosphere. Dry nitrogen was produced by passing the gas through a drying column filled with indicated drierite. *i*BVE (in n-hexane,  $1.0\text{ mol. dm}^{-3}$ ) was added to the flask. HCl gas was generated by dropping concentrated sulphuric acid into powdered sodium chloride and then dried by passing through concentrated sulphuric acid, activated charcoal and dry silica gel. The gaseous HCl was passed through *i*BVE solution and the reaction was continued for one hour at  $0\text{ }^{\circ}\text{C}$ . The excess HCl in the reaction mixture was removed by bubbling dry nitrogen gas through it. The quantitative formation of the pure adduct was confirmed by  $^1\text{H}$  NMR and the concentration of HCl-*i*BVE adduct was measured by the Volhard method. The solution was sealed into a brown bottle and stored in a freezer.

### Preparation of ester ended poly(methyl vinyl ether)

Polymerisation of MVE was carried out in a three-neck round bottom flask under dry nitrogen atmosphere in DCM. Polymerisation was initiated by introducing  $\text{TiCl}_4$  in DCM solution to the solution containing MVE, HCl-*i*BVE adduct (as an initiator) and **1** at  $-26\text{ }^{\circ}\text{C}$  and  $-78\text{ }^{\circ}\text{C}$ . The reaction mixture was stirred for 1.5 hours. The reaction was quenched with  $2.0\text{ mol. dm}^{-3}$  ammonia solution in methanol and diluted by addition of DCM. The polymer solution was washed sequentially with 2% HCl and deionised water (both below  $10\text{ }^{\circ}\text{C}$ ) to remove the titanium or tin containing residues. The solvent and unreacted reagents were removed by rotary-evaporation under reduced pressure and vacuum dried over-night to give the product.

### Preparation of poly(*isobutyl vinyl ether*) with an ester end group

Polymerisation of *i*BVE was carried out in a three-neck round bottom flask under dry nitrogen atmosphere in DCM. Polymerisation was initiated by introducing  $\text{SnCl}_4$  or  $\text{TiCl}_4$  in DCM solution to the solution containing *i*BVE, HCl-*i*BVE adduct (as an initiator) and **1**. The reaction mixture was stirred for 1.5 hours and then quenched with  $2.0\text{ mol. dm}^{-3}$  ammonia solution in methanol and diluted by addition of DCM. The polymer solution was washed sequentially with 2% HCl and deionised water (both below  $10\text{ }^{\circ}\text{C}$ ) to remove the titanium containing residues. The solvent and unreacted reagents were removed by rotary-evaporation under reduced pressure and vacuum dried over-night to give the product.

## Polymer characterisation

$^1\text{H}$  NMR spectra were recorded on a Bruker 250 MHz instrument at ambient temperature in deuterated chloroform. SEC measurements were carried out using a RI detector at ambient temperature with THF as the solvent and toluene as a flow marker. Polymer laboratories gel 2 x 60 cm low molecular weight columns were used, calibrated against polystyrene standards. Sample concentration was  $2.5 \text{ mg cm}^{-3}$ . MALDI-TOF mass spectra were obtained using a ToFSpec 2E instrument, Micromass, using dithranol as the matrix. The following parameters were used to analyse the polymer samples: Instrument voltage: 20KV, sampling rate: 500 MHz, pulse time: 39, pulse voltage: 2471 V, detector voltage: 1689 V, cationisation agent: NaI.

The end group masses were obtained from the MALDI-ToF mass spectra by plotting  $m/z$  against  $n$ . Where  $n$  is the degree of polymerisation. Then the end group masses were obtained by linear regression from

$$m/z = nM_r + (C + r) \quad \text{Equation 1}$$

Where  $M_r$  = monomer repeat mass;  $C$  = atomic mass of the cationising ion ( $\text{Na}^+$  or  $\text{K}^+$ ) and  $r$  = the sum of both end group masses.

Functionality was determined from the MALDI ToF mass spectra by obtaining the area of ion peaks corresponding to the target polymers within the total peak area  $\pm$  of  $m/z$  20 of the apex of the peak. For each target ion peak this produced a set of functionalities,  $F_i$ , corresponding to all of the degrees of polymerisation in the sample. The average functionality was then obtained by calculating the number average of these peaks. That is the percent functionality is given by:

$$F_n = 100 \times \frac{\sum F_i A_i}{\sum A_i} \quad \text{Equation 2}$$

Where,  $F_i$  = the functionality of the  $i$ th ion peak and  $A_i$  = the area of  $i$ th peak.

## References

1. Sun, Y.; Collett, J.; Fullwood, N.J.; MacNeil, S.; Rimmer, S. *Biomaterials*, 2007, **28**, 661.  
<https://doi.org/10.1016/j.biomaterials.2006.09.024>
2. Collett, J.; Crawford, A.; Hatton, P.V.; Geoghegan, M.; Rimmer, S. *J. Roy. Soc.-Interface*, 2007, **4**, 117.  
<https://doi.org/10.1098/rsif.2006.0158>
3. Rimmer, S.; Mohd. Ramli, A.N.; Lefèvre, S. *Polymer*, 1996, **37**, 4135.  
[https://doi.org/10.1016/0032-3861\(96\)00253-4](https://doi.org/10.1016/0032-3861(96)00253-4)
4. The Polyurethanes Book, D.; Lee, S. Eds. Wiley: New York, 2003. ISBN: 978-0-470-85041-1
5. Lo Verso, F.; Likos, C.N. *Polymer*, 2008, **49**, 1425.  
<https://doi.org/10.1016/j.polymer.2007.11.051>
6. Collins, S.; Rimmer, S. *React. Funct. Polym.*, 2006, **66**, 177.  
<https://doi.org/10.1016/j.reactfunctpolym.2005.07.014>
7. Pernecker, T.; Kennedy, J.P.; Ivan, B. *Macromolecules*, 1992, **25**, 1642.  
<https://doi.org/10.1021/ma00032a004>
8. Satoh, K.; Katayama, H.; Kamigaito, M.; Sawamoto, M. *ACS Symp. Ser.*, 1997, **665**, 106.  
<https://doi.org/10.1021/bk-1997-0665.ch010>
9. Miyamoto, M.; Sawamoto, M.; Higashimura, T. *Macromolecules*, 1984, **17**, 265.

- <https://doi.org/10.1021/ma00133a001>
10. Matyjaszewski, K. *Macromol. Symp.*, 1988, **13/14**, 433.  
<https://doi.org/10.1002/masy.19880130131>
  11. Pernecker, T.; Kennedy, J.P.; Ivan, B. *Macromolecules*, 1992, **25**, 1642.  
<https://doi.org/10.1021/ma00032a004>
  12. R. Faust, J.P. Kennedy, *Polym. Bull.*, 1986, **15**, 317.  
<https://doi.org/10.1007/BF00254850>
  13. Lang, W.; Rimmer, S. *Macromol. Rap. Comm.*, 2001, **22**, 194.  
[https://doi.org/10.1002/1521-3927\(200102\)22:3<194::AID-MARC194>3.0.CO;2-C](https://doi.org/10.1002/1521-3927(200102)22:3<194::AID-MARC194>3.0.CO;2-C)
  14. Sarker, P.K.; Rimmer, S. *Macromol. Chem. & Phys.*, 2005, **206**, 1280.  
<https://doi.org/10.1002/macp.200500128>
  15. Lang, W.; Sarker, P.K.; Rimmer, S. *Macromol. Chem. & Phys.*, 2004, **205**, 1011.  
<https://doi.org/10.1002/macp.200300198>
  16. England, R.M.; Rimmer, S. *Chem. Commun.*, 2010, **46**, 5767.  
<https://doi.org/10.1039/c0cc01705a>
  17. Fukui, H.; Deguchi, T.; Sawamoto, M.; Higashimura, T. *Macromolecules*, 1996, **29**, 1131.  
<https://doi.org/10.1021/ma946432+>
  18. Fukui, H.; Yoshihashi, S.; Sawamoto, M.; Higashimura, T. *Macromolecules*, 1996, **29**, 1862.  
<https://doi.org/10.1021/ma946436e>
  19. Fukui, H.; Sawamoto, M.; Higashimura, T. *Macromolecules*, 1996, **28**, 3756.  
<https://doi.org/10.1021/ma00115a002>
  20. Fukui, H.; Sawamoto, M.; Higashimura, T. *Macromolecules* 1994, **27**, 1297.  
<https://doi.org/10.1021/ma00084a002>
  21. Fukui, H.; Sawamoto, M.; Higashimura, T. *Macromolecules* 1993, **26**, 7315.  
<https://doi.org/10.1021/ma00078a030>
  22. Tasdelen, M. A.; Kahveci, M. U.; Yagci, Y. *Progr. Polym. Sci.* 2011, **36**, 455.  
<https://doi.org/10.1016/j.progpolymsci.2010.10.002>
  23. Rajanbabu, T.V. *J. Org. Chem.* 1984, **49**, 2083.  
<https://doi.org/10.1021/jo00186a001>
  24. Mayr, H.; Bug, T.; Gotta, M.F.; Hering, N.; Irrgang, B.; Janker, B.; Kempf, B.; Loos, R.; Ofial, A. R.; Remennikov, G.; Schimmel, H. *J. Am. Chem. Soc.*, 2001, **123**, 9500.  
<https://doi.org/10.1021/ja010890y>
  25. Burfeindt, J.; Patz, M.; Müller, M.; Mayr, H. *J. Am. Chem. Soc.*, 1998, **120**, 3629.  
<https://doi.org/10.1021/ja974003w>
  26. Van Durme, K.; Van Mele, B.; Bernaerts, K. V.; Verdonck, B.; Du Prez, F. E. *J Polym Sci Part B: Polym. Phys.* 2006, **44**, 461.  
<https://doi.org/10.1002/polb.20710>
  27. Subira, F.; Sauvet, G.; Vairon, J-P.; Sigwalt, P. *J. Polym. Sci. Symp.* 1976, **56**, 221.  
<https://doi.org/10.1002/polc.5070560123>
  28. Subira, F.; Vairon, J-P.; Sigwalt, P. *Macromolecules*, 1988, **21**, 2339.  
<https://doi.org/10.1021/ma00186a007>
  29. Ohmura, T.; Sawamoto, M.; Higashimura, T. *Macromol* 1994, **27** 3714.  
<https://doi.org/10.1021/ma00092a006>
  30. Lang, W.; Rimmer, S. *Macromol. Symp.*, 2002, **184**, 311.

[https://doi.org/10.1002/1521-3900\(200208\)184:1<311::AID-MASY311>3.0.CO;2-8](https://doi.org/10.1002/1521-3900(200208)184:1<311::AID-MASY311>3.0.CO;2-8)

31. Katayama, H.; Kamigaito, M.; Sawamoto, M. *J. Polym. Sci. A: Polym. Chem.*, 2001, **39**, 1249.

<https://doi.org/10.1002/pola.1102>

32. Katayama, H.; Kamigaito, M.; Sawamoto, M. , *J Polym Sci A: Polym Chem.*, 2001, **39**, 1258.

<https://doi.org/10.1002/pola.1103>

This paper is an open access article distributed under the terms of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>)