

## Supplementary Material

### Mixed matrix membranes derived from a spirobifluorene polymer of intrinsic microporosity and polyphenylene networks for the separation of toluene from dimethyl sulfoxide

Richard A. Kirk,<sup>a</sup> Chunchun Ye,<sup>b</sup> Andrew B. Foster,<sup>a</sup> Alexey V. Volkov,<sup>c</sup> Neil B. McKeown,<sup>\*b</sup> and Peter M. Budd<sup>\*a</sup>

<sup>a</sup>Department of Chemistry, University of Manchester, Manchester M13 9PL, UK;


<sup>b</sup>EastChem, School of Chemistry, University of Edinburgh, David Brewster Road, Edinburgh EH9 3FJ, UK;

<sup>c</sup>A.V. Topchiev Institute of Petrochemical Synthesis, 29 Leninsky Av., Moscow 119991, Russian Federation.

Email: [Peter.Budd@manchester.ac.uk](mailto:Peter.Budd@manchester.ac.uk); [neil.mckeown@ed.ac.uk](mailto:neil.mckeown@ed.ac.uk)

#### Table of Contents

<b>Figure S1.</b> Nitrogen adsorption and desorption isotherms at 77 K.....	S2
<b>Table S1.</b> Pervaporation: Membrane thicknesses, fluxes and separation factors.....	S3
<b>Table S2.</b> Pervaporation: Fluxes normalised for membrane thickness.....	S3

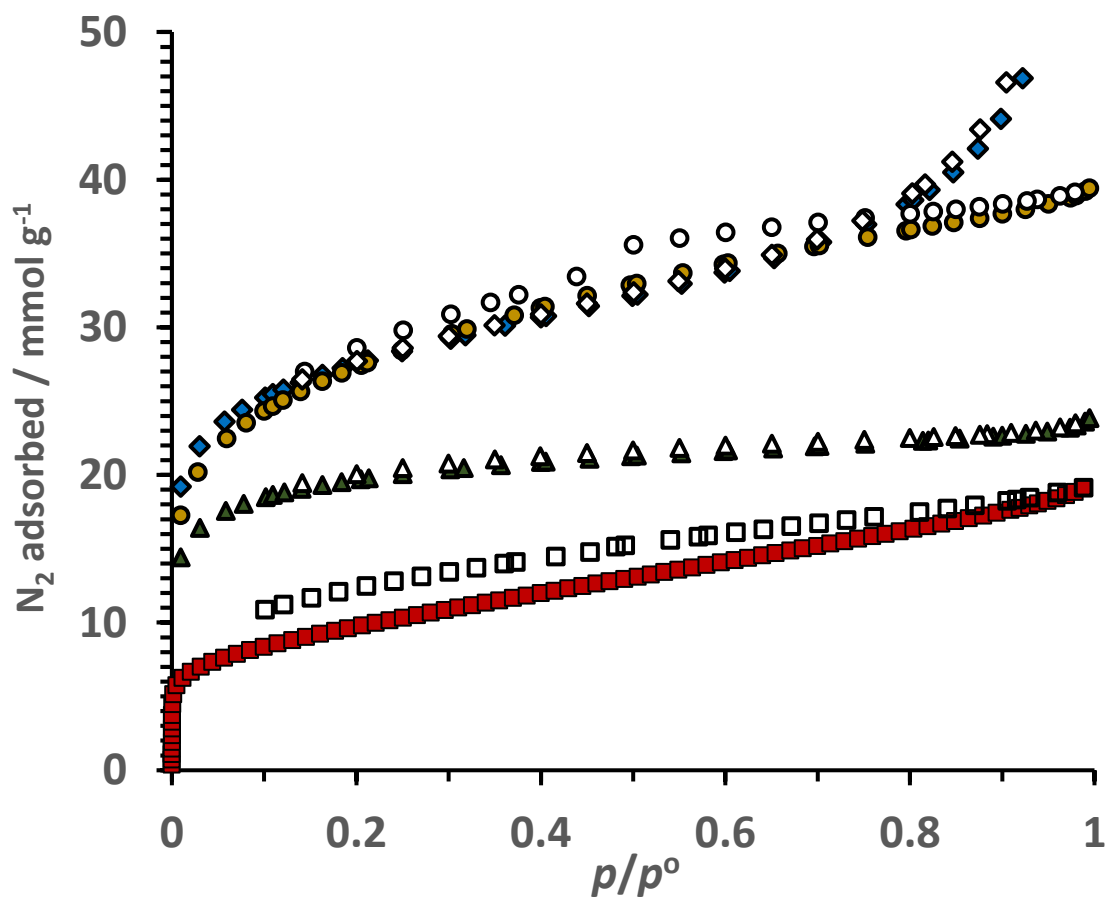

**Figure S1.** Nitrogen adsorption (solid symbols) and desorption (open symbols) isotherms at 77 K for powdered samples of PIM-SBF (squares) and of polyphenylene networks prepared from HPB (triangles), OPQ (diamonds) and TPB (circles).

**Table S1.** Pervaporation of toluene/DMSO mixture (77:23 volume ratio) at 65°C: Membrane thicknesses, fluxes and separation factors

Membrane material	Thickness ( $\mu\text{m}$ )	Total flux ( $\text{kg m}^{-2} \text{h}^{-1}$ )	Toluene flux ( $\text{kg m}^{-2} \text{h}^{-1}$ )	DMSO flux ( $\text{kg m}^{-2} \text{h}^{-1}$ )	Separation Factor $\beta$
SBF-PIM	43	1.992	1.813	0.179	3.87
SBF-PIM + 5 wt% OPQ	100	3.081	2.795	0.286	3.79
SBF-PIM + 5 wt% TPB	120	8.12	7.119	1.001	2.83
SBF-PIM + 5 wt% HPB	100	1.205	1.127	0.078	5.46

**Table S2.** Pervaporation of toluene/DMSO mixture (77:23 volume ratio) at 65°C: Fluxes normalised for membrane thickness

Membrane material	Normalised total flux ( $\text{kg } \mu\text{m m}^{-2} \text{h}^{-1}$ )	Normalised toluene flux ( $\text{kg } \mu\text{m m}^{-2} \text{h}^{-1}$ )	Normalised DMSO flux ( $\text{kg } \mu\text{m m}^{-2} \text{h}^{-1}$ )
SBF-PIM	85.66	77.96	7.697
SBF-PIM + 5 wt% OPQ	308.1	279.5	28.60
SBF-PIM + 5 wt% TPB	974.4	854.3	120.1
SBF-PIM + 5 wt% HPB	120.5	112.7	7.800